

840
12/12/2
TECHNICAL NOTES
NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

No. 840

LIBRARY COPY

JUL 9 1942
1942
LANGLEY RESEARCH CENTER
LIVERPOOL, NASA
HAMPTON, VIRGINIA

**TENSILE AND PACK COMPRESSIVE TESTS OF SOME SHEETS OF
ALUMINUM ALLOY, 1025 CARBON STEEL, AND CHROMIUM-NICKEL STEEL**

By C. S. Atchison and James A. Miller
National Bureau of Standards

~~REFINED DOCUMENT~~

~~This document contains classified information affecting
the national defense of the United States within the
meaning of the Espionage Act (Sec 503) and 32.
It is the intent of the revelation of its contents in
whole or in part to an unauthorized person is prohibited by
law. Information so classified may be imparted only
to persons in the military and naval Services of the
United States, appropriate civilian officers and employees
of the Federal Government who have a legitimate interest
therein, and to United States citizens of known loyalty and
discipline who of necessity must be informed thereof.~~

FOR REFERENCE

Washington
February 1942

~~NOT TO BE DESTROYED UNTIL 1960~~

NATIONAL ADVISORY COMMITTEE FOR AERONAUTICS

TECHNICAL NOTE NO. 840

TENSILE AND PACK COMPRESSIVE TESTS OF SOME SHEETS OF
ALUMINUM ALLOY, 1025 CARBON STEEL, AND CHROMIUM-NICKEL STEEL

By C. S. Aitchison and James A. Miller

SUMMARY

Tensile and compressive stress-strain curves, stress-deviation curves, and secant modulus-stress curves are given for longitudinal and transverse specimens of 17S-T, 24S-T, and 24S-RT aluminum-alloy sheet in thicknesses from 0.032 to 0.081 inch, 1025 carbon steel sheet in thicknesses of 0.054 and 0.120 inch, and chromium-nickel steel sheet in thicknesses from 0.020 to 0.0275 inch.

Significant differences were found between the tensile and the compressive stress-strain curves, and also the corresponding corollary curves; similarly, differences were found between the curves for the longitudinal and transverse directions. These differences are of particular importance in considering the compressive strength of aircraft structures made of thin sheet. They are explored further for the case of compression by giving tangent modulus-stress curves in longitudinal and transverse compression and dimensionless curves of the ratio of tangent modulus to Young's modulus and of the ratio of reduced modulus for a rectangular section to Young's modulus, both plotted against the ratio of stress to secant yield strength.

INTRODUCTION

A knowledge of the tensile and the compressive properties of thin sheet metal is essential for the efficient design of many parts of aircraft structures. The compressive properties are of particular importance because the design of most of these structures is dictated by compressive rather than tensile strength.

A serious difficulty in obtaining the compressive

properties of thin sheet metal is the tendency of the sheet to buckle at a stress well below the yield strength. This difficulty is overcome to a large extent by the pack method developed in recent years at the National Bureau of Standards with the support of the National Advisory Committee for Aeronautics and the Bureau of Aeronautics, Navy Department (references 1 and 2). Preliminary tests of a number of sheet materials used in aircraft showed that large differences may exist between the tensile and compressive properties. There were also appreciable differences for specimens taken lengthwise of the sheet and those taken crosswise.

For this reason it seemed desirable to obtain the tensile and compressive properties of sheet metals used in aircraft, to evaluate these differences, and to provide an experimental background for a study and classification of stress-strain data. The National Advisory Committee for Aeronautics accordingly requested the National Bureau of Standards to carry out such an investigation.

The present paper gives the results of tensile and pack compressive tests on specimens taken from some aluminum alloy and steel sheets in the direction of the length of the sheet and in the direction of the width. These results are presented for purposes of comparison rather than for use as typical properties of the materials. It is hoped that a continuation of this study will result in obtaining parameters or analytical expressions that will provide a better description of the stress-strain relationship of some of these materials than those in use at present.

MATERIAL

The description of the sheet materials is given in table I. The sheets having as their source NACA were surplus sheets from other investigations for the National Advisory Committee for Aeronautics (references 3, 4, and 5). The sheets having as their source Navy Department were materials submitted from time to time by the Bureau of Aeronautics, Navy Department, for mechanical tests. The authors take this opportunity to thank the Navy Department for permission to include this material in the present paper.

Table II gives the chemical composition of the chromium-nickel steel as supplied by the manufacturers.

TENSILE TESTS

The tensile specimens were taken from each sheet in the lengthwise direction (longitudinal) and crosswise (transverse). They were type 5 specimens described in reference 6 and complied with specifications in reference 7.

The tensile specimens were tested in beam and poise, screw type, testing machines. They were held in Templin grips.

The strain was measured by a pair of Tuckerman 2-inch optical strain gages. These gages were attached to opposite faces of the reduced section when the specimen was under an initial load.

The tensile stress-strain curves are shown in figures 1 to 20. The figure numbers correspond to the sheet numbers. The origin for each curve was obtained from an extrapolation to zero stress by a least-square line fitted by factorial moments (reference 8).

The stress-deviation curves were obtained by the method proposed by Tuckerman (reference 9). For each sheet the trail modulus was the experimental value of Young's modulus in longitudinal tension.

The secant modulus-stress curves were plotted from secant moduli obtained by dividing each value of stress by the corresponding value of strain.

The results of the tensile tests and the tensile properties prescribed in current Navy Department specifications are given in table III.

The experimental value of Young's modulus for each specimen from the aluminum alloys, from the carbon steel, and also for each transverse specimen from the chromium-nickel steels was taken as the slope of a least-square straight line fitted to the lower portion of the stress-strain curve. For each longitudinal specimen from the chromium-nickel steels, the value of Young's modulus was taken as the slope of a least-square parabola at the origin.

The yield strengths by the offset method were obtained

from the stress-strain curves and the experimental values of Young's modulus given in table III.

The yield strengths by the extension-under-load method were obtained from the stress-strain curves and the values given in table III of strain prescribed in the specifications for the extension-under-load method.

Sheets 1 to 13, comprising the aluminum alloys and the carbon steel, complied with the tensile requirements in current specifications. Sheets 14, 15, and 16 of chromium-nickel steel passed current tensile specification requirements for 1/4-hard, 1/2-hard, and 3/4-hard temper, respectively, and are considered as such in this report. Sheets 17, 18, 19, and 20, of chromium-nickel steel passed current tensile specification requirements for full-hard temper with the exception that the elongation value for sheet 17 was 3.0 percent, not the prescribed 4.0 percent. These sheets are considered as full-hard temper in this report.

PACK COMPRESSIVE TESTS

The compressive tests of the aluminum alloy and the carbon steel sheets were made by the pack method described in reference 1. The compressive tests of the chromium-nickel steel sheets were made in accordance with the extension of the pack method described in reference 2.

The specimens for the packs were taken from each sheet in the longitudinal direction and in the transverse direction. The number of specimens in each pack is given in table IV.

The packs were tested in a vertical, fluid-support, Bourdon-tube, hydraulic-type, universal testing machine of 100 kips capacity.

The strain was measured by a pair of Tuckerman 1-inch optical strain gages. These gages were attached on each side of the pack to the edge of the middle specimen when the pack was under an initial load.

The compressive stress-strain curves, the stress-deviation curves, and the secant modulus-stress curves are shown in the figures.

The tangent modulus-stress curves were faired through a number of points, each being an arbitrarily selected value of tangent modulus plotted against the corresponding value of stress. Each value of stress was obtained on the stress-strain or the stress-deviation curve by moving a straight-edge, oriented to correspond to the given value of tangent modulus, into tangency with the curve.

In order to facilitate the comparison of the shapes of the tangent-modulus curves for the different materials, nondimensional tangent modulus-stress curves are also shown. These curves were plotted from values obtained by dividing the tangent moduli by Young's modulus and by dividing the stresses by the yield strength, secant method. The yield strength, secant method (after Osgood, reference 10) was selected so that the nondimensional curves could be used for materials the compressive stress-strain curves of which are affinely related to any of the stress-strain curves obtained from these sheets.

The reduced modulus-stress curves for a rectangular cross section are also shown as nondimensional curves. These curves were plotted from values obtained by dividing the reduced moduli by Young's modulus and by dividing the stresses by the yield strength, secant method. The reduced modulus for a rectangular section (reference 11) is given by the following formula:

$$E_r = \frac{4 E E_\sigma}{(\sqrt{E} + \sqrt{E_\sigma})^2}$$

where

E_r = reduced modulus

E = Young's modulus

E_σ = tangent modulus

The results of the compressive tests are given in table IV.

Young's modulus for each specimen was taken as the slope of a least-square straight line fitted to the lower portion of the stress-strain curve.

The yield strengths, offset method, were obtained

from the stress-strain curves and the experimental values of Young's modulus given in table IV.

The yield strengths, secant method, were obtained from the stress-strain curves and the values of secant modulus* given in table IV.

For sheets 1 to 13, comprising the aluminum alloys and carbon steel, the values of compressive yield strength, both longitudinal and transverse, were greater than the specified minimum values for tensile yield strength.

For sheets 14 to 19, of chromium-nickel steels, the longitudinal compressive yield strengths were less than the specified tensile yield strengths. The transverse compressive yield strengths, however, were greater than the specified values. For sheet 20 of chromium-nickel steel, the values of compressive yield strength, both in the longitudinal direction and in the transverse direction, were greater than the specified tensile yield strength for the full-hard temper. For the convenience of readers interested in the compressive properties of the chromium-nickel steels, the information supplied by the manufacturers regarding the chemical composition of sheets 14 to 20 is given in table II.

CONCLUSIONS

The materials considered in this report passed current tensile specification requirements with the exception of a longitudinal elongation value from one sheet. Since the tensile properties usually exceeded the specified minimum values by large amounts, the results cannot be considered as representative of material just meeting specifications.

For the aluminum alloys the yield strengths as determined either by the offset method or by the extension-under-load method were nearly the same for each tensile specimen. Likewise, the yield strengths as determined by the offset method and by the secant method were nearly

*The values of secant modulus were obtained, as suggested by Osgood in reference 12, by multiplying Young's modulus by a constant for the material so chosen that, for a tensile specimen just passing specifications, the yield strength obtained by the secant method would be equal to the specified minimum yield strength.

NACA Technical Note No. 840

7

the same for each pack. The closest agreement of yield strengths was between the transverse tensile and the longitudinal compressive values; the difference did not exceed 5.2 percent. In each case there was an appreciable difference in the shapes of the curves even when there was little difference between yield strengths.

For the carbons steels, the longitudinal yield strengths were nearly the same in tension and in compression and the transverse yield strengths were nearly the same. There were, however, marked differences in the yield strength with direction.

In the case of the chromium-nickel steels, the differences between the tensile and compressive properties and between the compressive properties in the two directions were especially pronounced. Owing to the gradual curvature of the stress-strain curves and the differences between the experimental values and the specification values for Young's modulus and yield strength, the values for yield strength obtained by the extension-under-load method differed from those obtained by the offset method by amounts up to 9 percent. With the exception of the yield strength of the stress-relieved specimen, which was well above the minimum value specified for tensile yield strength, the longitudinal compressive yield strengths obtained by the secant method were lower than the corresponding values obtained by the offset method by amounts up to 26 percent. This difference was ascribed to the gradual curvature of the stress-strain curves and to the lack of correspondence between the longitudinal compressive yield strengths and the values specified for the tensile yield strengths. On the other hand, the yield strengths for the transverse packs were above those specified for the longitudinal tensile specimens and the values obtained by the secant method were higher than those obtained by the offset method.

The results given in this paper emphasize the need for further consideration of definitions of yield strength for materials with gradually curving stress-strain curves.

In general, the appreciable differences in the shapes of the longitudinal tensile, the transverse tensile, the longitudinal compressive, and the transverse compressive stress-strain curves and their corollary curves suggest that they cannot be used interchangeably in precise design.

REFERENCES

1. Aitchison, C. S., and Tuckerman, L. B.: The "Pack" Method for Compressive Tests of Thin Specimens of Materials Used in Thin-Wall Structures. Rep. No. 649, NACA, 1939.
2. Aitchison, C. S.: Extension of Pack Method for Compressive Tests. T.N. No. 789, NACA, 1940.
3. Brueggeman, Wm. C.: Mechanical Properties of Aluminum-Alloy Rivets. T.N. No. 585, NACA, 1936.
4. Brueggeman, W. C.: Strength of Welded Aircraft Joints. Rep. No. 584, NACA, 1937.
5. Brueggeman, W. C., and Roop, Frederick O.: Mechanical Properties of Flush-Riveted Joints. Rep. No. 701, NACA, 1940.
6. Anon.: General Specification for Inspection of Metals. Federal Specification QQ-M-151a, Federal Standard Stock Catalog, sec. IV; pt. 5, Nov. 27, 1936.
7. Standard Methods of Tension Testing of Metallic Materials (E8-36). A.S.T.M. Standards, 1936.
8. Sasuly, Max: Trend Analysis of Statistics. The Brookings Institution, 1934, ch. XIII.
9. Tuckerman, L. B.: Discussion of paper by R. L. Templin, The Determination and Significance of the Proportional Limit in the Testing of Metals. A.S.T.M., Proc., vol. XXIX, pt. II, 1929, pp. 538-46.
10. Osgood, W. R.: A Rational Definition of Yield Strength. Jour. Appl. Mech., vol. 7, no. 2, June 1940, pp. A-61-A-62.
11. von Kármán, Th.: Untersuchungen über Knickfestigkeit, Mitteilungen über Forschungsarbeiten. Ver. deutsch. Ing., Heft 81, 1910.
12. Osgood, William R.: Column Strength of Tubes Elastically Restrained against Rotation at the Ends. Rep. No. 615, NACA, 1938.

TABLE I.-- DESCRIPTION OF MATERIALS TESTED

Sheet	Description	Nominal thickness of sheet (in.)	Source	Navy specifications	
				When material was acquired	Current
1	Aluminum alloy 17S-T	.032	NACA	47A3b	47A3c
2	do	.051	do	do	do
3	Aluminum alloy 24S-T	.032	Navy Dept.	47A10	47A10d
4	do	.064	do	do	do
5	do	.081	do	do	do
6	Aluminum alloy 24S-RT	.032	NACA	47A10INT	do
7	do	.032	Navy Dept.	47A10a	do
8	do	.051	NACA	47A10INT	do
9	do	.064	Navy Dept.	47A10a	do
10	do	.081	NACA	47A10INT	do
11	do	.081	Navy Dept.	47A10a	do
12	1025 carbon steel	.054	NACA	47S17a	AN-QQ-S-651
13	do	.120	do	do	do
14	Chromium-nickel steel	.020	Navy Dept.	47S21	47S21a
15	do	.020	do	do	do
16	do	.020	do	do	do
17	do	.020	do	do	do
18	do	.020	do	do	do
19	do	.024	do	do	do
20	do	.0275	do	do	do

TABLE II
CHEMICAL COMPOSITION OF CHROMIUM-NICKEL STEELS,
AS SUPPLIED BY THE MANUFACTURERS

Sheet	Carbon (percent)	Manganese (percent)	Chromium (percent)	Nickel (percent)
14	0.11	0.76	17.8	7.8
15	.10	.72	17.4	7.5
16	.13	.63	17.5	7.3
17	.08	.35	18.4	8.0
18	.13	.34	17.0	7.0
19	.13	.38	17.1	7.2
a20	.12	.47	17.96	7.01

^aThe manufacturer of sheet 20 stated that it had a stress-relieving heat treatment after cold rolling.

TABLE III.—RESULTS OF TENSILE TESTS

Sheet	Material	Nominal thickness of sheet (in.)	Direction	Specification values					Test results				
				Strain prescribed for yield strength, extension under load	Young's modulus (kips/sq in.)	Minimum yield strength (kips/sq in.)	Minimum tensile strength (kips/sq in.)	Minimum elongation in 2 inches (percent)	Young's modulus (kips/sq in.)	Yield strength		Tensile strength (kips/sq in.)	Elongation in 2 inches (percent)
										Offset method, offset = 0.2 percent	Extension under load method		
1	Aluminum alloy 178-T	0.032	Longitudinal	0.0058	10,000	38.0	66.0	18.0	10,400	40.1	40.0	56.7	20.5
			Transverse	.0058	10,000	38.0	66.0	18.0	10,300	34.8	34.4	57.8	19.0
2	—do—	.061	Longitudinal	.0052	10,000	38.0	66.0	16.0	10,530	41.6	41.4	60.7	20.5
			Transverse	.0052	10,000	38.0	66.0	18.0	10,370	36.2	35.8	59.3	20.5
3	Aluminum alloy 248-T	.032	Longitudinal	.0060	10,000	40.0	82.0	15.0	10,600	55.2	54.7	70.4	18.0
			Transverse	.0060	10,000	40.0	82.0	15.0	10,300	48.1	47.0	87.7	18.0
4	—do—	.064	Longitudinal	.0060	10,000	40.0	82.0	17.0	10,500	52.1	51.8	69.3	19.5
			Transverse	.0060	10,000	40.0	82.0	17.0	10,400	45.8	45.1	68.3	19.0
5	—do—	.061	Longitudinal	.0060	10,000	40.0	82.0	17.0	10,420	53.1	52.8	70.8	19.0
			Transverse	.0060	10,000	40.0	82.0	17.0	10,300	44.1	43.8	68.1	18.5
6	Aluminum alloy 848-R7	.032	Longitudinal	.0070	10,000	50.0	85.0	11.0	10,500	61.8	61.5	73.5	17.5
			Transverse	.0070	10,000	50.0	85.0	11.0	10,500	54.3	54.0	71.5	18.5
7	—do—	.038	Longitudinal	.0070	10,000	50.0	85.0	11.0	10,410	55.8	55.2	76.2	18.5
			Transverse	.0070	10,000	50.0	85.0	11.0	10,500	55.8	55.8	74.7	14.5
8	—do—	.061	Longitudinal	.0070	10,000	50.0	85.0	12.0	10,440	63.0	62.5	76.3	18.0
			Transverse	.0070	10,000	50.0	85.0	12.0	10,500	55.5	55.2	73.0	15.5
9	—do—	.084	Longitudinal	.0070	10,000	50.0	85.0	12.0	10,450	63.4	62.8	75.0	15.0
			Transverse	.0070	10,000	50.0	85.0	12.0	10,510	55.8	55.2	72.4	15.0
10	—do—	.061	Longitudinal	.0070	10,000	50.0	85.0	12.0	10,440	58.8	58.2	74.8	18.5
			Transverse	.0070	10,000	50.0	85.0	12.0	10,500	56.4	56.0	78.7	18.0
11	—do—	.081	Longitudinal	.0070	10,000	50.0	85.0	12.0	10,470	63.8	63.4	74.7	18.5
			Transverse	.0070	10,000	50.0	85.0	12.0	10,480	58.8	58.2	78.1	15.5
12	1085 carbon steel	.064	Longitudinal	.0043	b30,000	36.0	68.0	11.0	30,060	61.6	61.6	78.1	20.0
			Transverse	.0043	30,000	36.0	55.0	11.0	31,620	64.1	64.1	77.6	20.0
13	—do—	.120	Longitudinal	.0043	30,000	36.0	68.0	15.0	30,370	58.8	52.6	69.7	24.0
			Transverse	.0043	30,000	36.0	68.0	14.0	31,140	58.1	56.1	71.6	22.5
14	Chromium-nickel steel	.080	Longitudinal	.00488	28,000	75.0	125.0	25.0	28,190	106.4	97.9	174.3	33.5
			Transverse	(d)	(d)	(d)	(d)	(d)	28,780	96.8	93.1	173.3	33.0
15	—do—	.020	Longitudinal	.00823	28,000	110.0	180.0	10.0	28,840	126.2	123.8	154.0	27.5
			Transverse	(d)	(d)	(d)	(d)	(d)	28,070	121.1	121.7	157.4	22.0
16	—do—	.020	Longitudinal	.00719	28,000	135.0	175.0	5.0	27,960	143.6	143.0	188.8	22.5
			Transverse	(d)	(d)	(d)	(d)	(d)	28,640	137.4	140.6	193.2	20.5
17	—do—	.020	Longitudinal	.00738	28,000	140.0	185.0	4.0	28,770	173.6	167.5	199.3	3.0
			Transverse	(d)	(d)	(d)	(d)	(d)	29,010	168.7	160.3	204.1	6.5
18	—do—	.020	Longitudinal	.00738	28,000	140.0	185.0	4.0	27,940	176.5	162.2	204.3	17.0
			Transverse	(d)	(d)	(d)	(d)	(d)	29,060	160.3	158.0	211.7	11.5
19	—do—	.024	Longitudinal	.00738	28,000	140.0	185.0	4.0	27,920	158.8	153.8	188.6	18.5
			Transverse	(d)	(d)	(d)	(d)	(d)	28,000	149.7	151.8	193.0	17.5
20	—do—	.0275	Longitudinal	.00738	28,000	140.0	185.0	4.0	27,230	169.5	160.5	197.7	14.0
			Transverse	(d)	(d)	(d)	(d)	(d)	31,030	180.4	178.5	204.6	11.0

^aComputed from specified yield strength, specified extension under load and an offset of 0.2 percent.

^bComputed from specified yield strength, specified extension under load and an offset of 0.3 percent.

^cComputed in conformity with the value of Young's modulus prescribed in current specification.







^dThe current specification applies only to longitudinal specimens. When required, the value prescribed for the longitudinal specimen was used for the transverse specimen.

TABLE IV.- RESULTS OF PACK COMPRESSIVE TESTS

Sheet	Material	Nominal thickness of sheet (in.)	Direction	Number of specimens in a pack	Young's modulus (kips/sq in.)	Secant modulus (kips/sq in.)	Yield strength	
							Offset method, offset = 0.2 percent (kips/sq in.)	Secant method (kips/sq in.)
1	Aluminum alloy 178-T	0.032	Longitudinal	13	10,530	6,480	33.4	33.3
			Transverse	13	10,460	6,440	37.4	37.7
2	do	.051	Longitudinal	5	10,570	6,510	35.4	35.6
			Transverse	5	10,580	6,510	39.6	40.8
3	Aluminum alloy 248-T	.032	Longitudinal	13	10,680	7,120	46.5	47.1
			Transverse	13	10,620	7,080	50.4	51.1
4	do	.064	Longitudinal	5	10,650	7,100	44.0	44.3
			Transverse	5	10,710	7,140	49.1	49.7
5	do	.081	Longitudinal	5	10,610	7,080	43.3	43.6
			Transverse	6	10,650	7,100	47.8	48.3
6	Aluminum alloy 248-RT	.032	Longitudinal	13	10,800	7,720	51.4	51.1
			Transverse	13	10,750	7,680	57.5	57.8
7	do	.032	Longitudinal	13	10,840	7,740	55.7	55.9
			Transverse	17	10,760	7,680	61.4	61.9
8	do	.051	Longitudinal	7	10,680	7,630	53.8	53.9
			Transverse	7	10,730	7,670	59.3	59.7
9	do	.084	Longitudinal	7	10,760	7,680	55.1	55.3
			Transverse	7	10,770	7,700	60.4	61.0
10	do	.081	Longitudinal	5	10,780	7,680	53.6	53.7
			Transverse	5	10,760	7,680	60.3	60.8
11	do	.081	Longitudinal	5	10,780	7,680	54.0	54.1
			Transverse	5	10,740	7,680	60.3	60.8
12	1026 carbon steel	.064	Longitudinal	5	30,780	8,780	59.7	59.8
			Transverse	5	32,680	9,330	63.8	63.8
13	do	.120	Longitudinal	5	31,310	8,940	52.0	52.3
			Transverse	5	31,790	9,080	56.1	56.3
14	Chromium-nickel steel	.020	Longitudinal	31	28,070	18,580	73.5	70.3
			Transverse	31	28,980	17,110	121.8	134.9
15	do	.020	Longitudinal	31	28,100	19,080	72.5	59.1
			Transverse	31	29,860	19,860	138.7	139.8
16	do	.020	Longitudinal	31	27,610	19,930	83.4	61.8
			Transverse	31	28,980	20,930	165.4	169.7
17	do	.020	Longitudinal	31	28,120	19,040	97.9	81.7
			Transverse	31	29,860	21,630	191.2	199.1
18	do	.020	Longitudinal	31	27,370	19,860	111.0	95.4
			Transverse	31	29,860	21,380	197.5	208.2
19	do	.024	Longitudinal	25	27,390	19,900	91.4	75.0
			Transverse	25	29,810	21,370	181.0	186.7
20	do	.0275	Longitudinal	23	27,600	20,120	181.6	164.9
			Transverse	23	31,580	23,020	202.3	207.7

^aBuckled at 61.0 kips/sq in. stress, yield strength obtained by extrapolation.

NACA T.N. 840

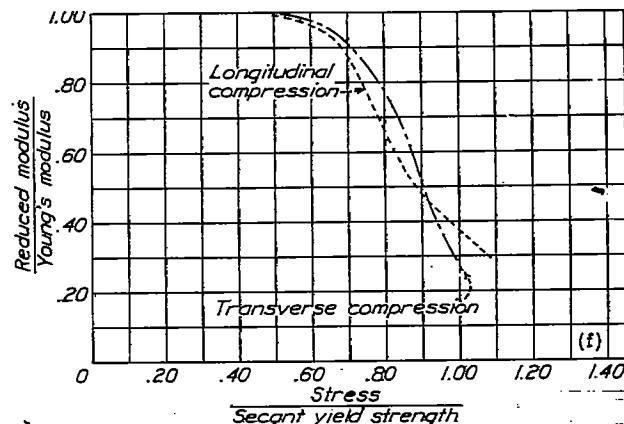
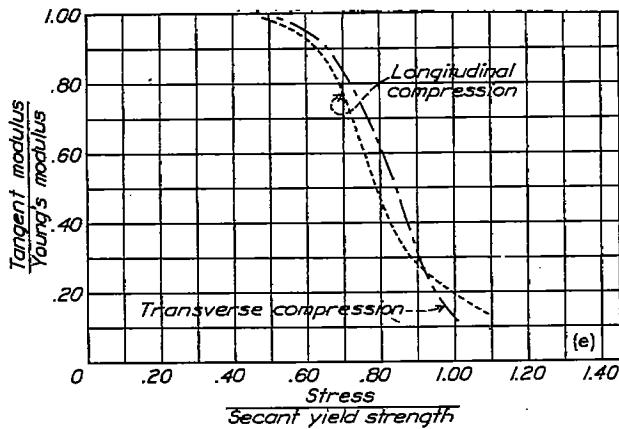
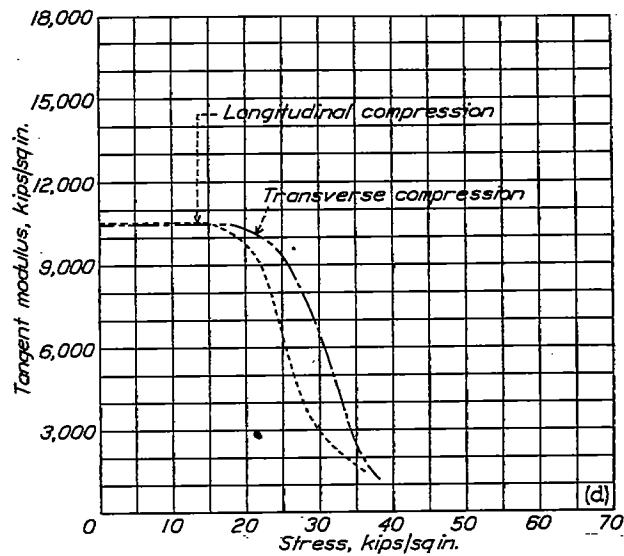
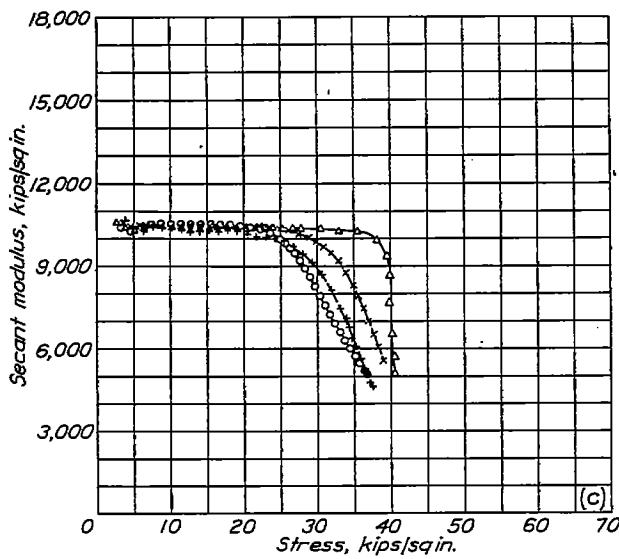
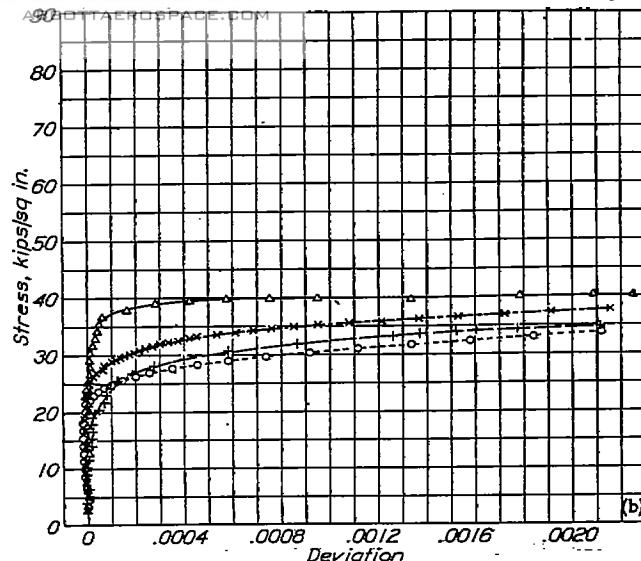
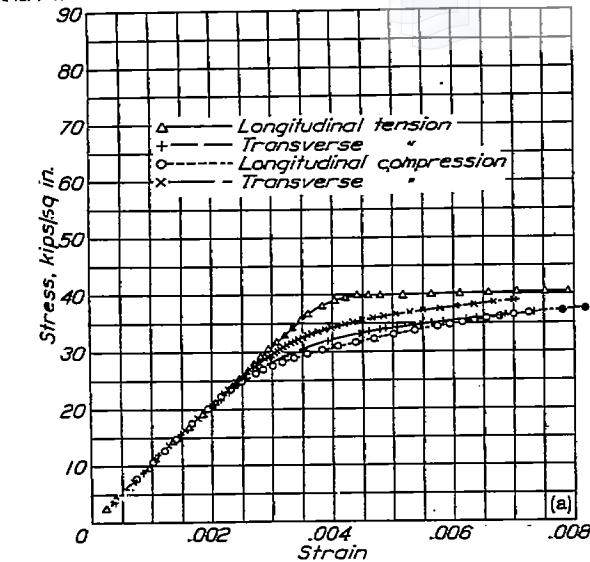


- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 1.- Sheet 1. Aluminum alloy 17S-T; thickness, 0.032 inch.

NACA T.N. 840

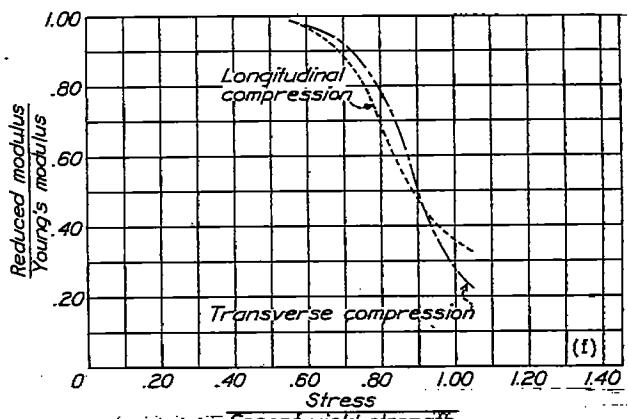
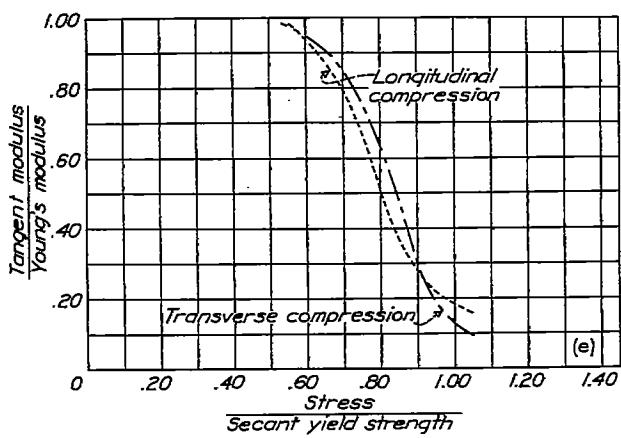
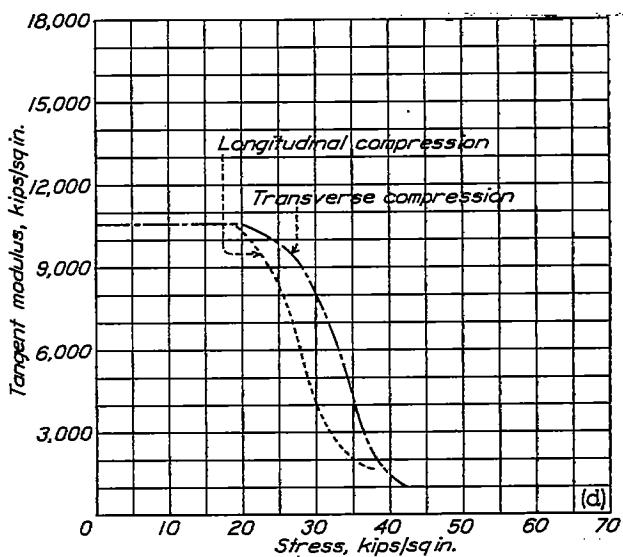
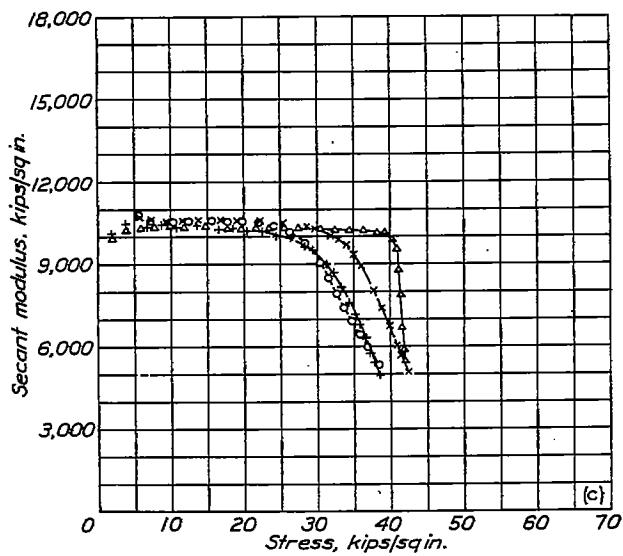
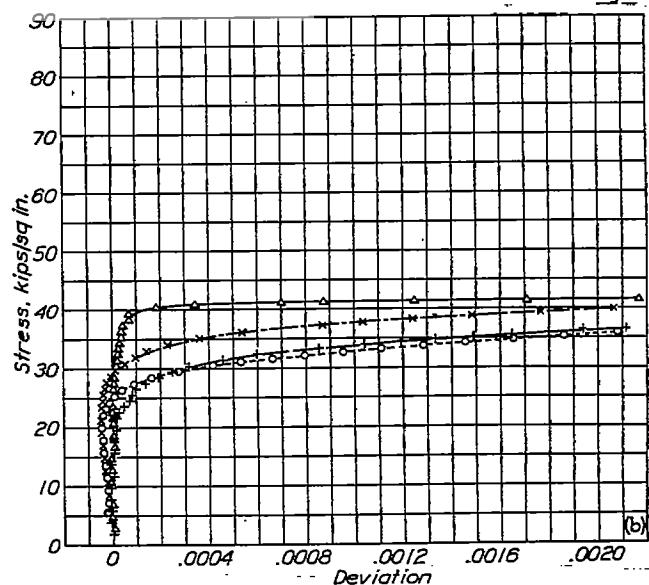
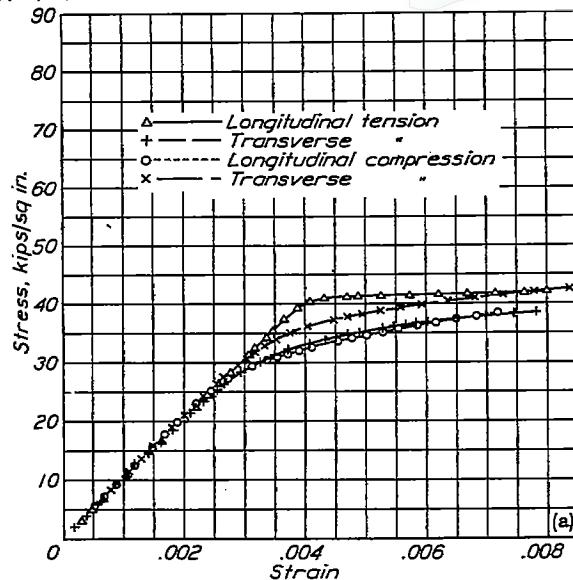


- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 2.- Sheet 2. Aluminum alloy 175-T; thickness, 0.051 inch.

NACA T.N. 840

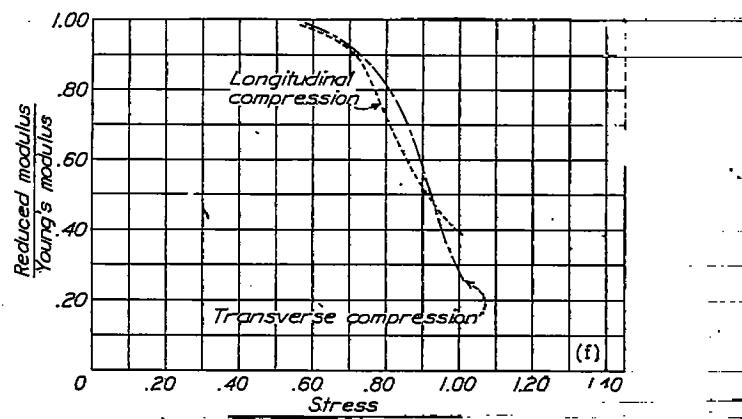
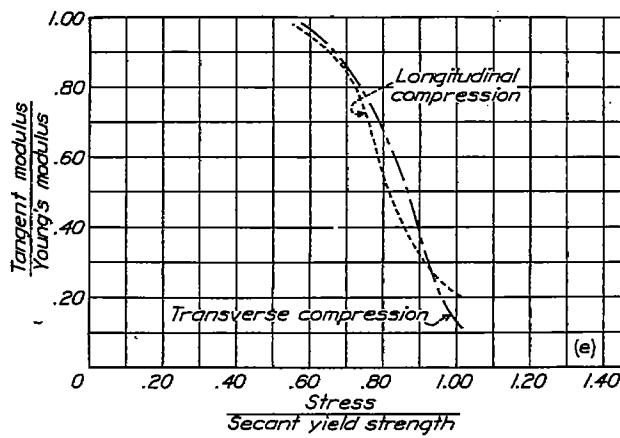
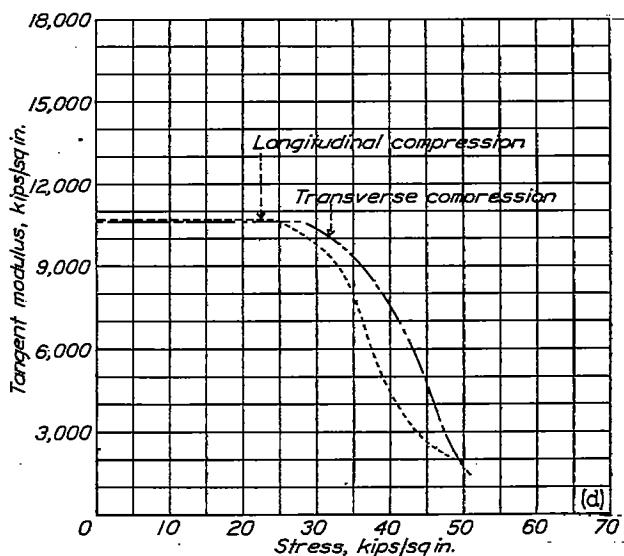
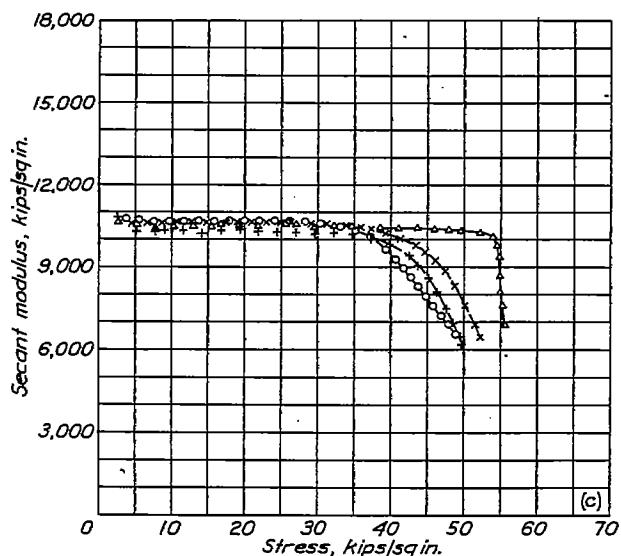
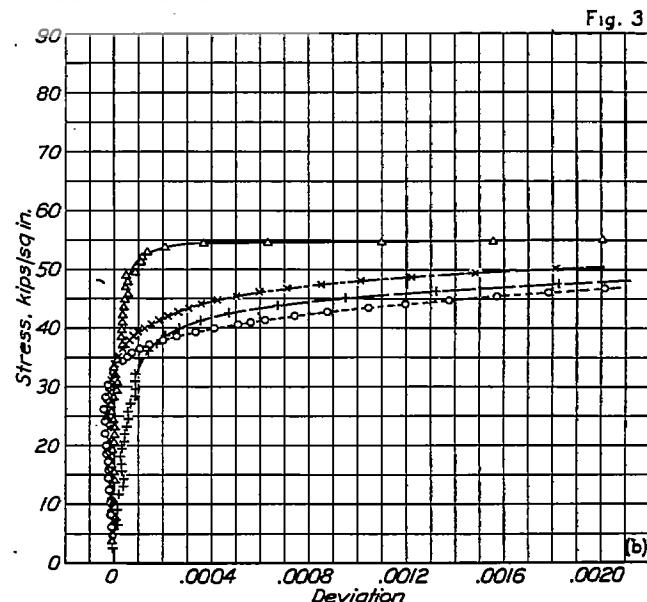
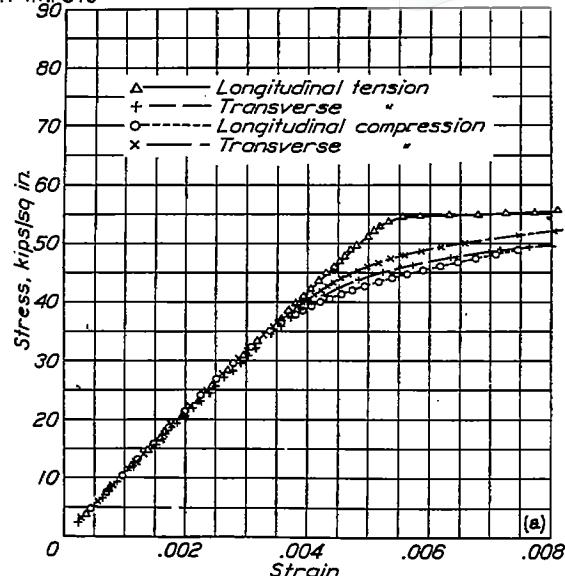


- (a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus - stress curves.

Figure 3.- Sheet 3. Aluminum alloy 24S-T; thickness, 0.032 inch.

NACA T.N. 840

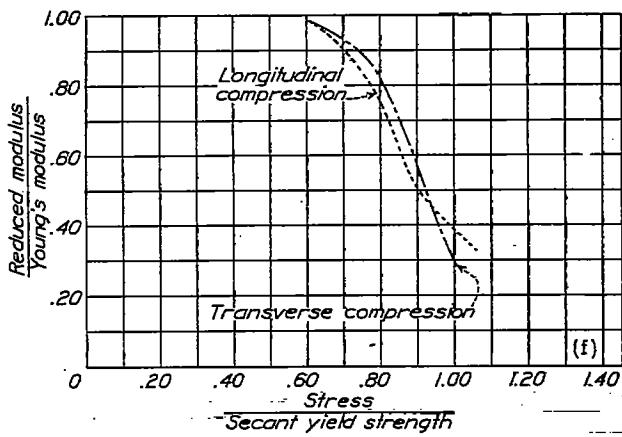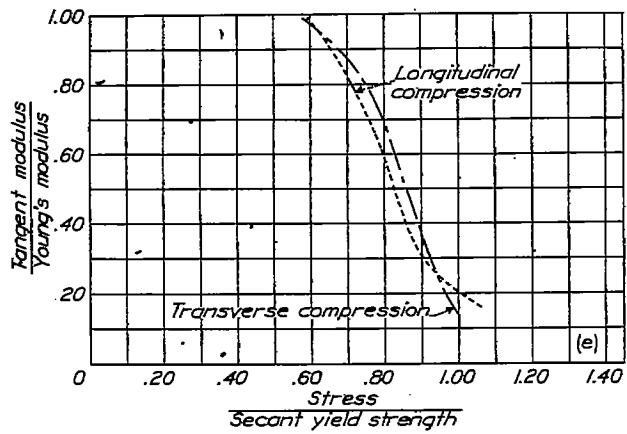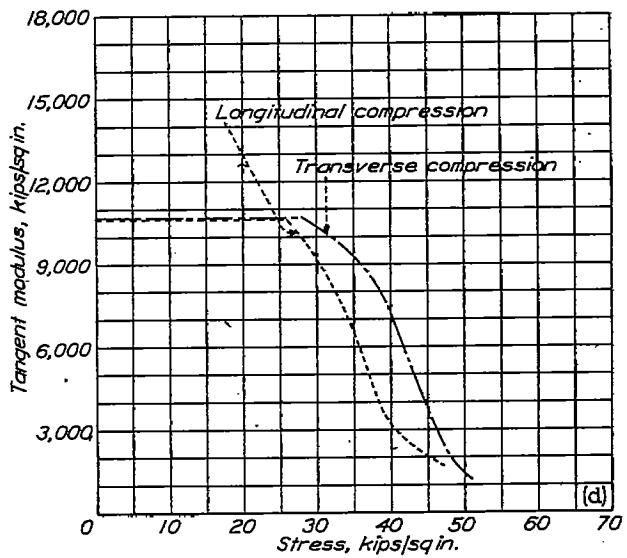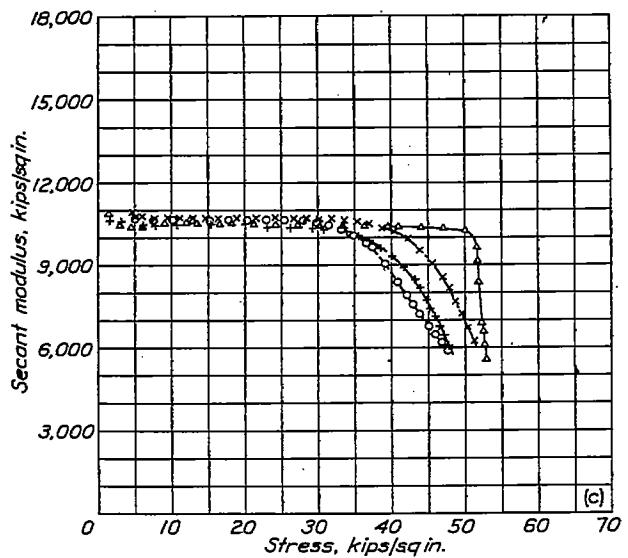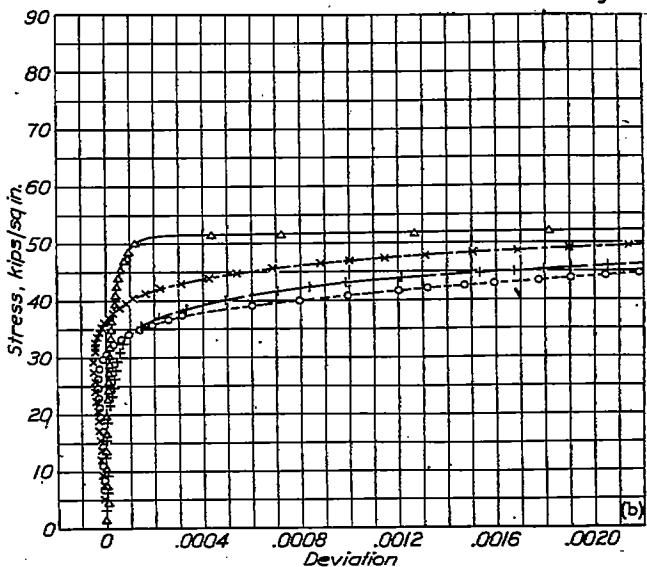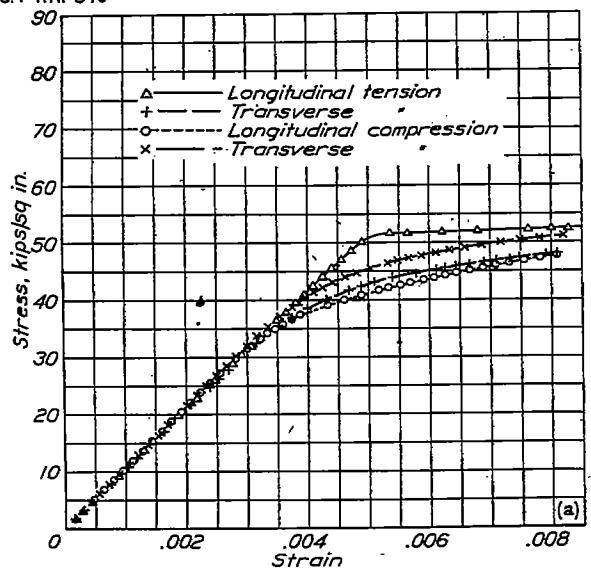

- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.







- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 4.- Sheet 4. Aluminum alloy 248-T; thickness, 0.064 inch.

Fig. 4

NACA T.N. 840

Fig. 5

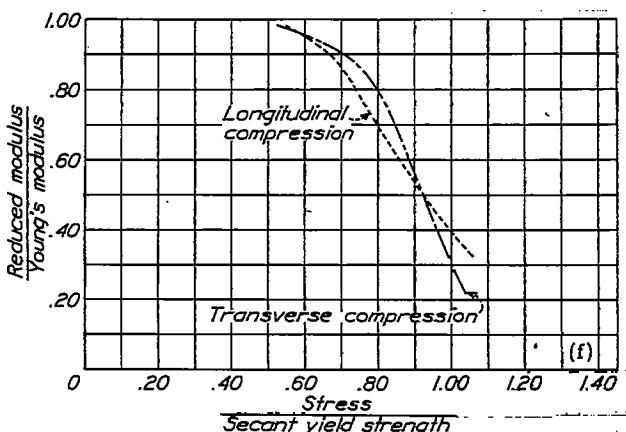
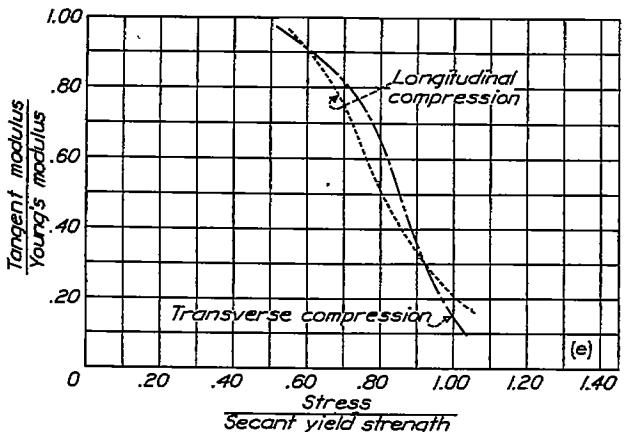
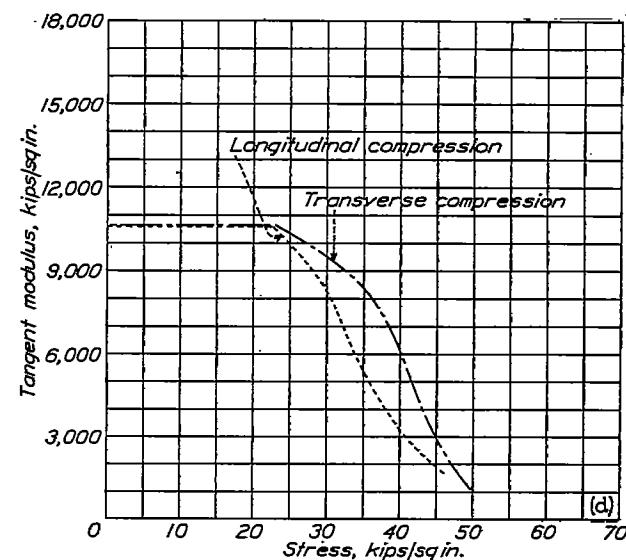
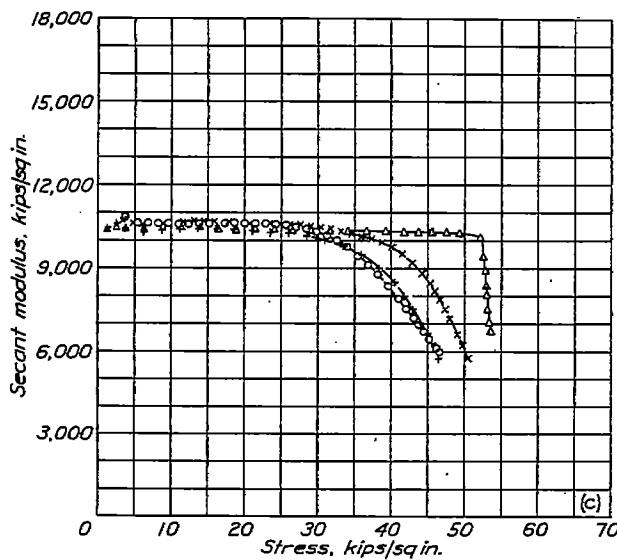
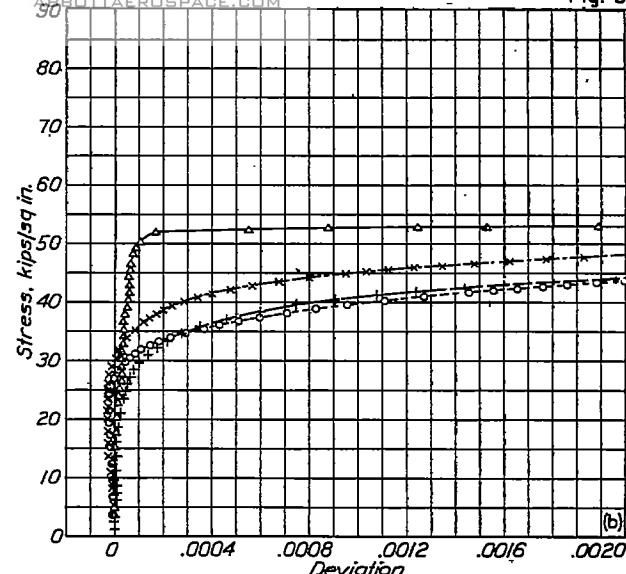
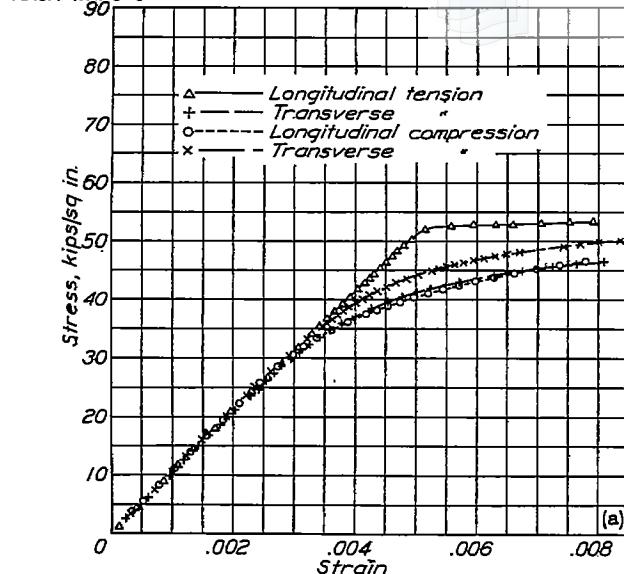


- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 5.- Sheet 5. Aluminum alloy 24S-T; thickness, 0.081 inch.

NACA T.N. 840

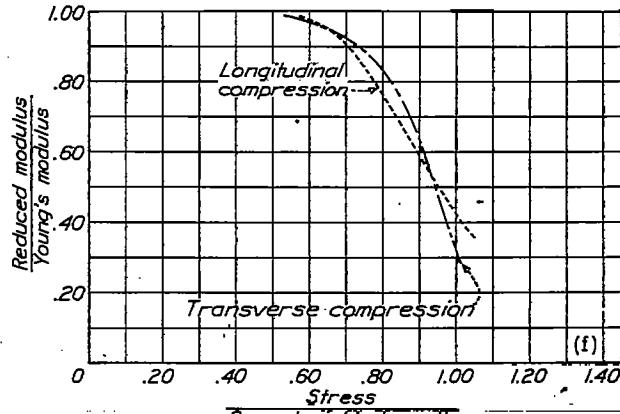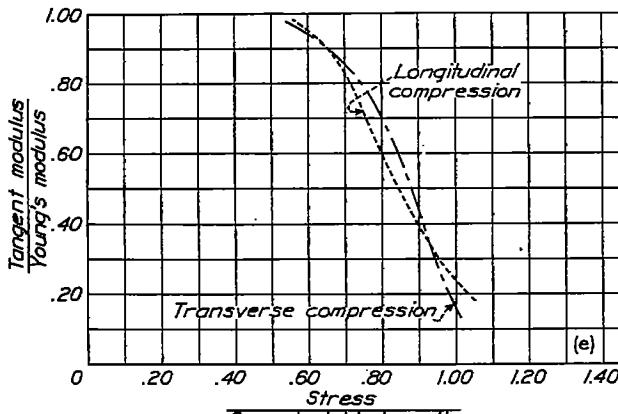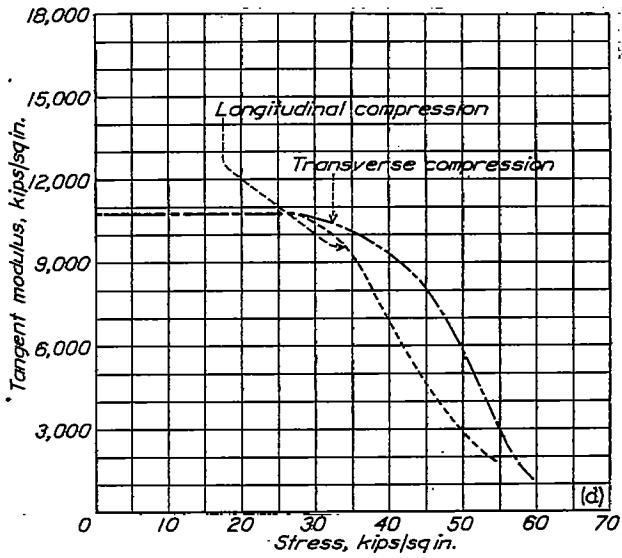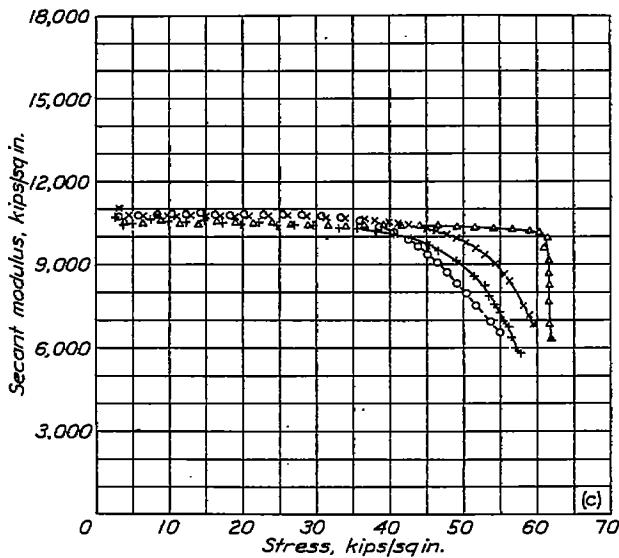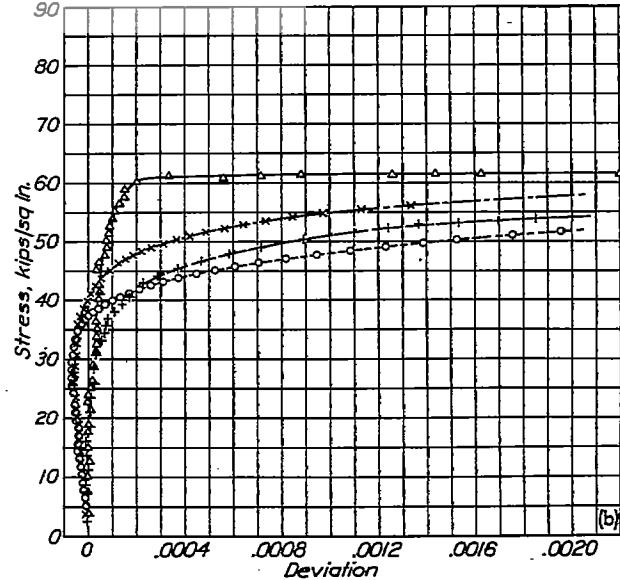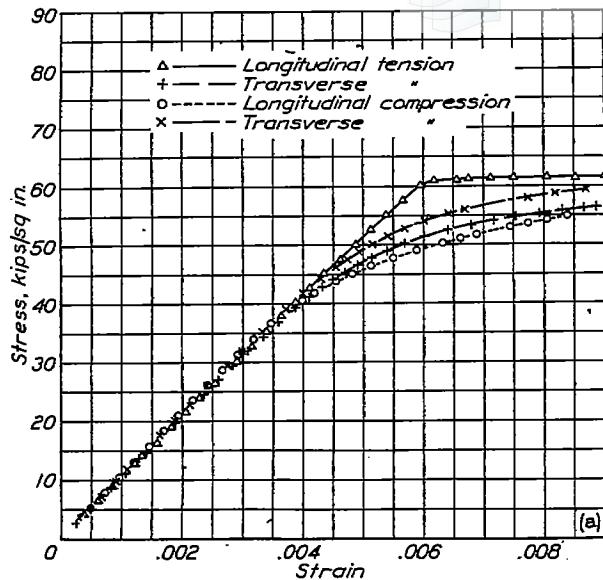







- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 6.- Sheet 6. Aluminum alloy 24S-RT; thickness, 0.032 inch.

NACA T.N. 840

Fig. 7

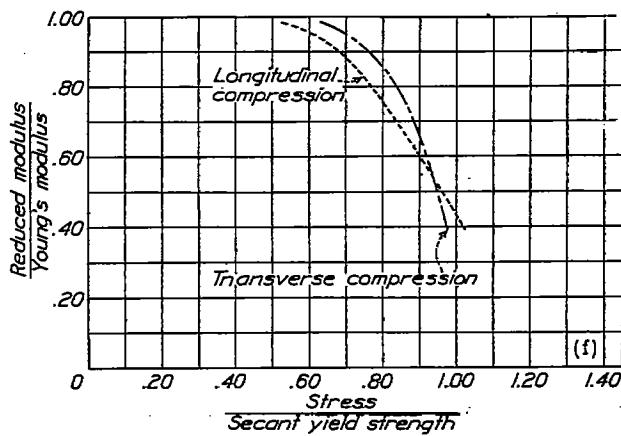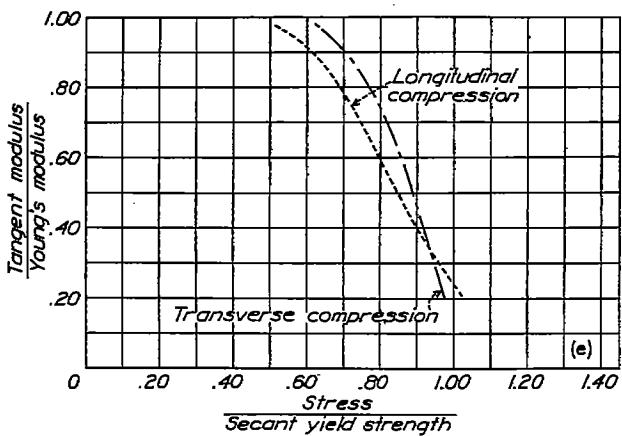
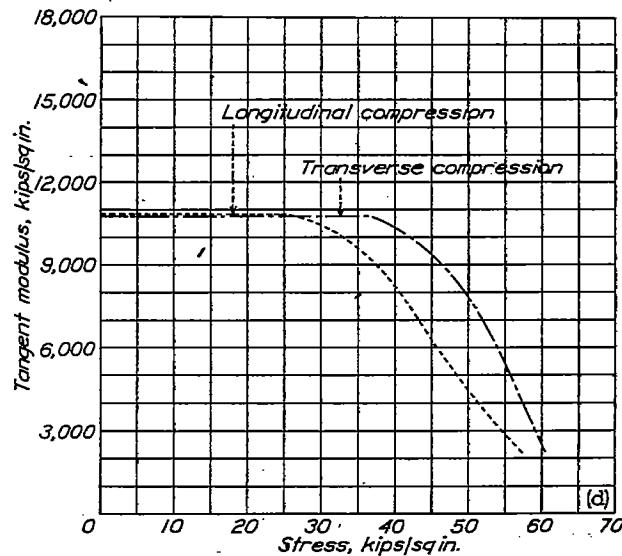
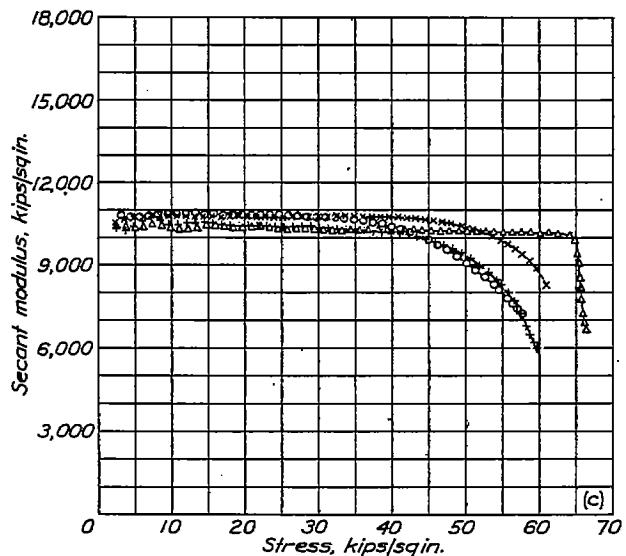
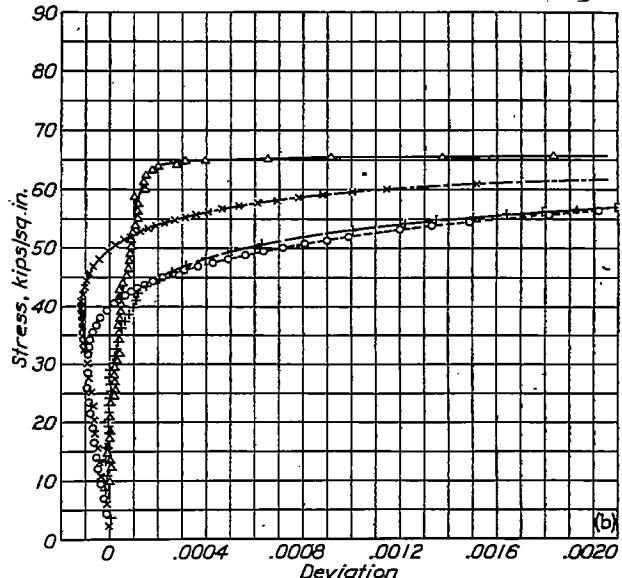
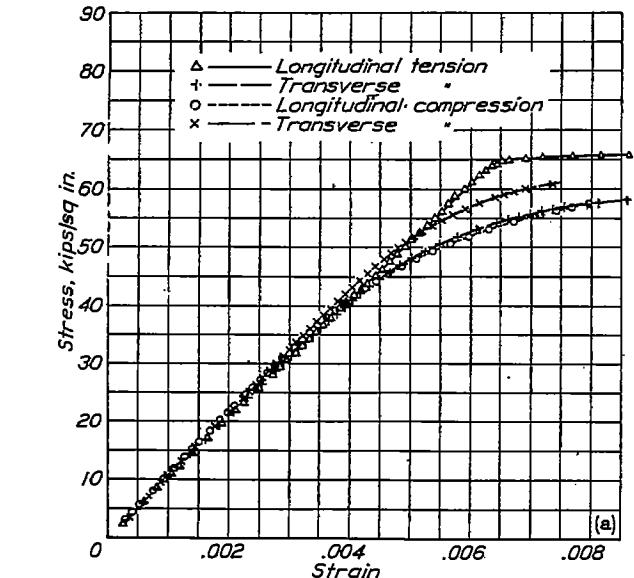


- (a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.


- (b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 7.- Sheet 7. Aluminum alloy 24S-RT; thickness, 0.032 inch.

NACA T.N. 840

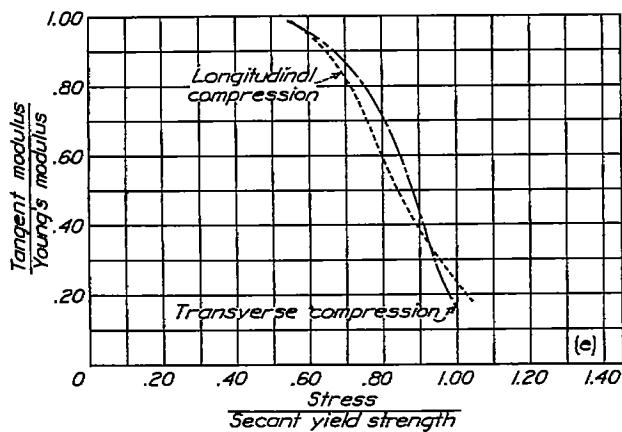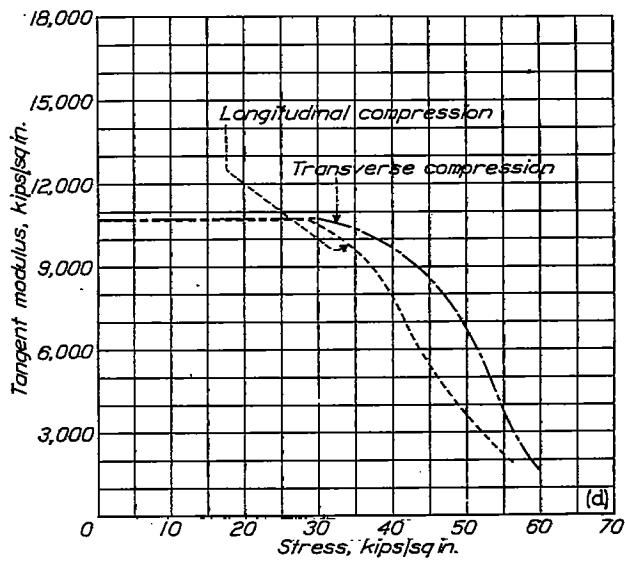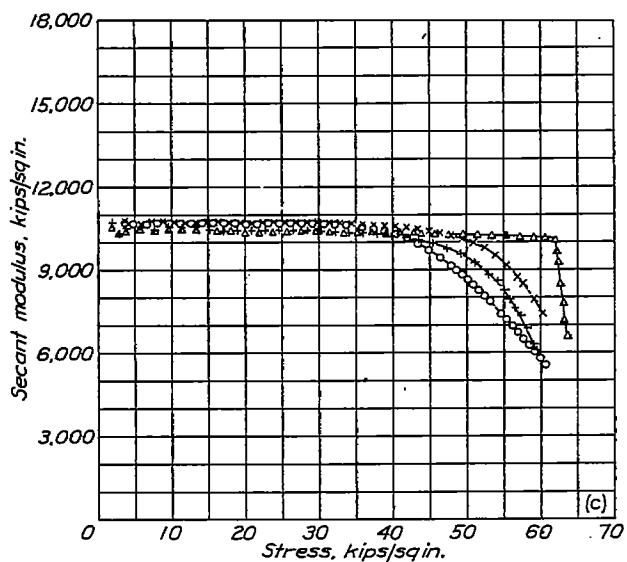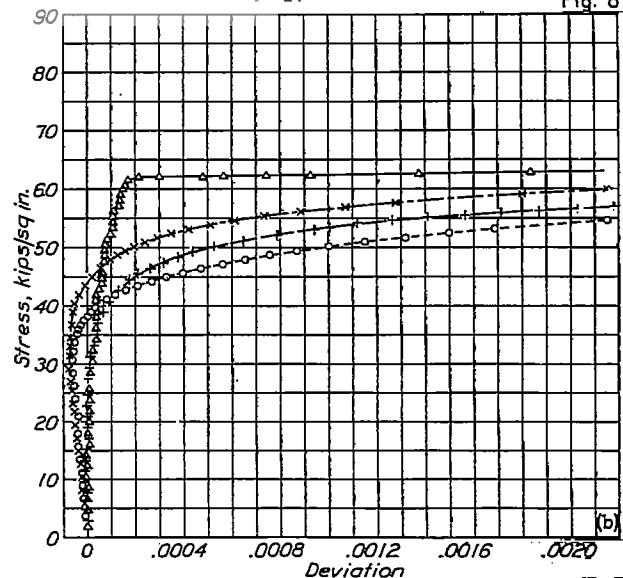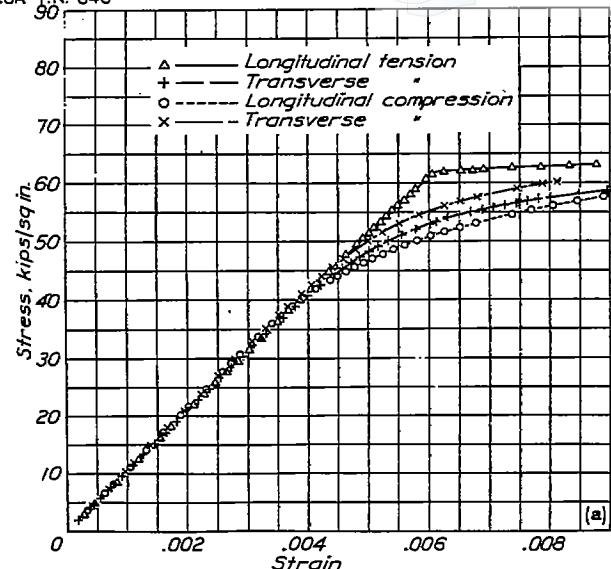

(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.






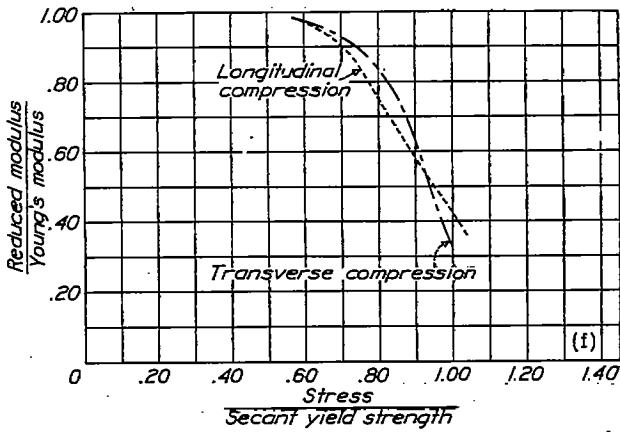


(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 8.- Sheet 8. Aluminum alloy 248-RT; thickness, 0.051 inch.

NACA T.N. 840

Fig. 9

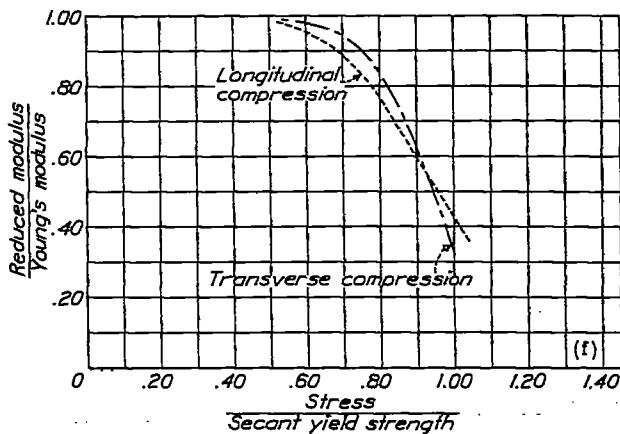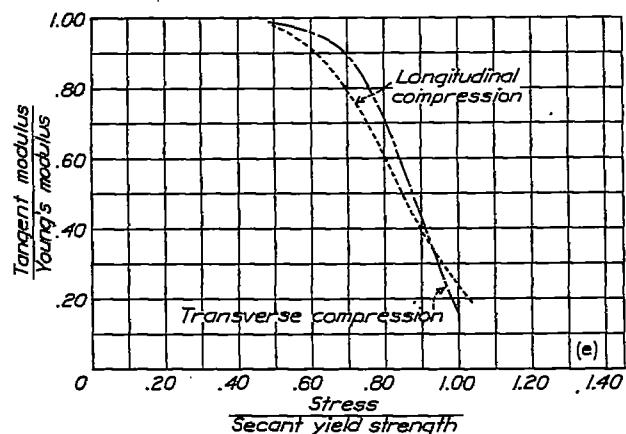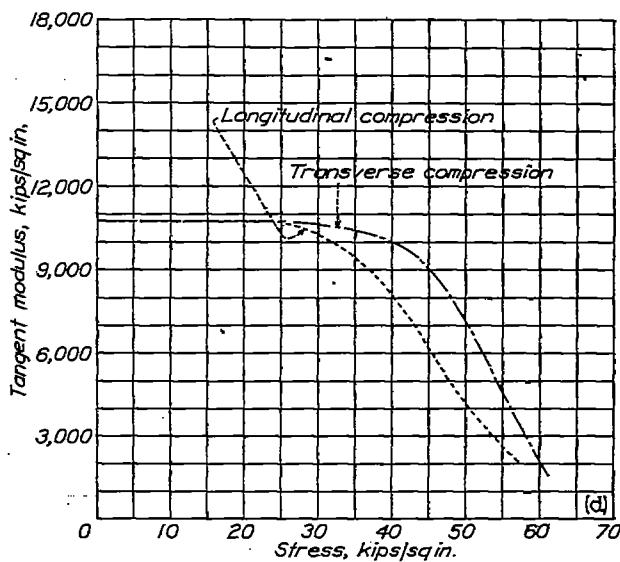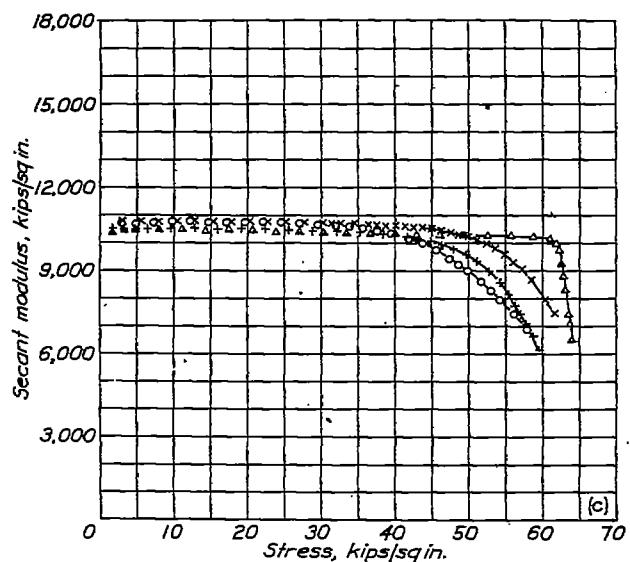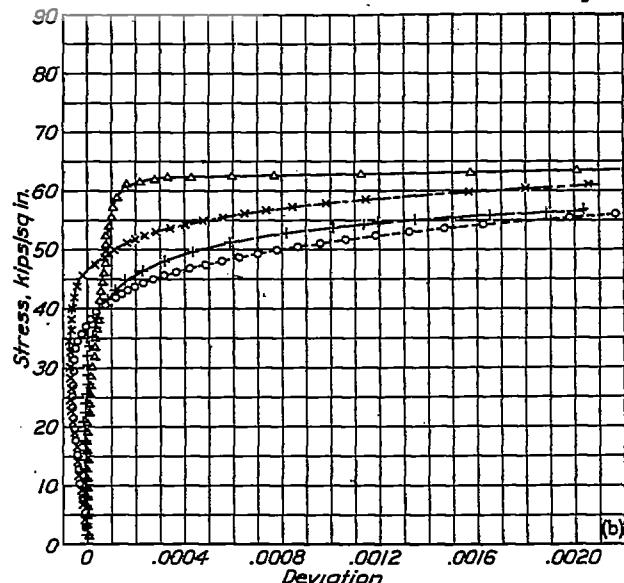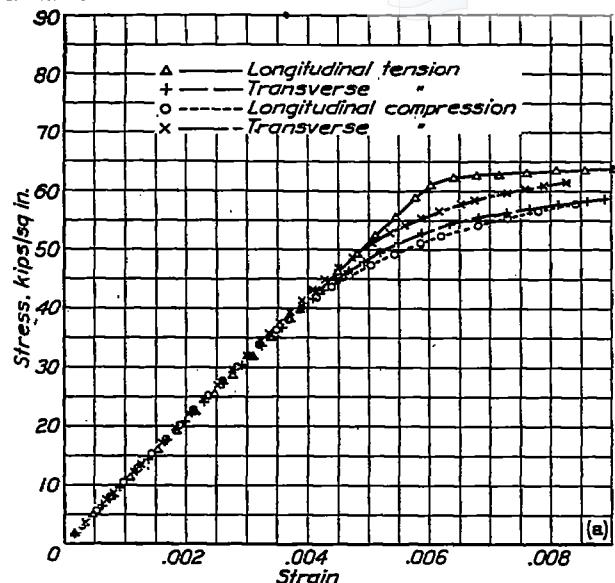

- (a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 9.- Sheet 9. Aluminum alloy 248-RT; thickness, 0.064 inch.

NACA T.N. 840












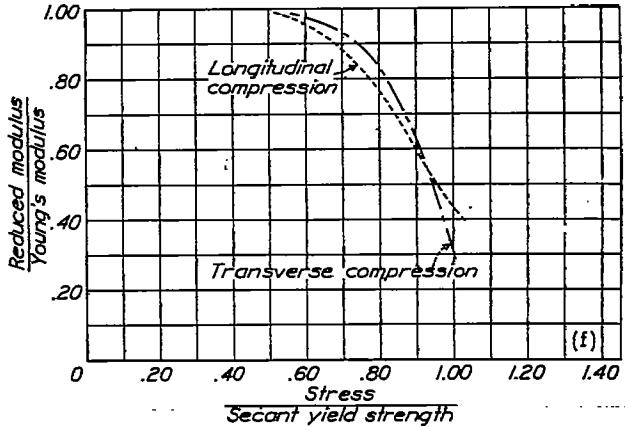


Figure 10.- Sheet 10. Aluminum alloy 24S-RT; thickness, 0.081 inch.

NACA T.N. 840

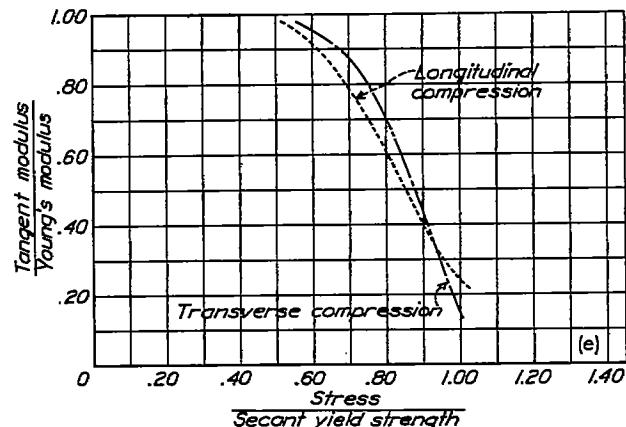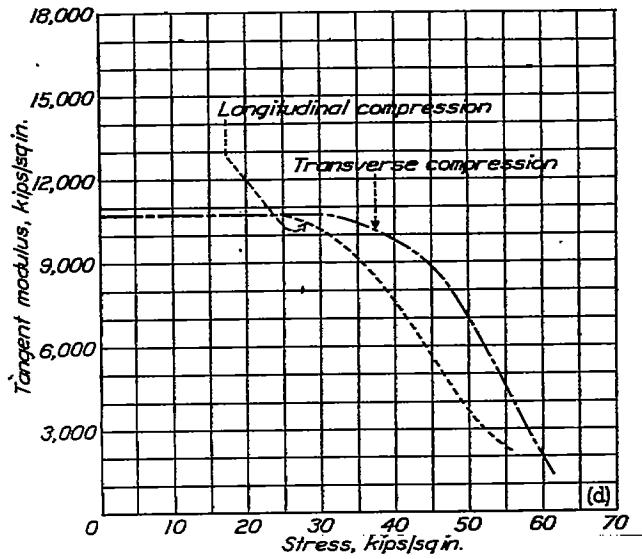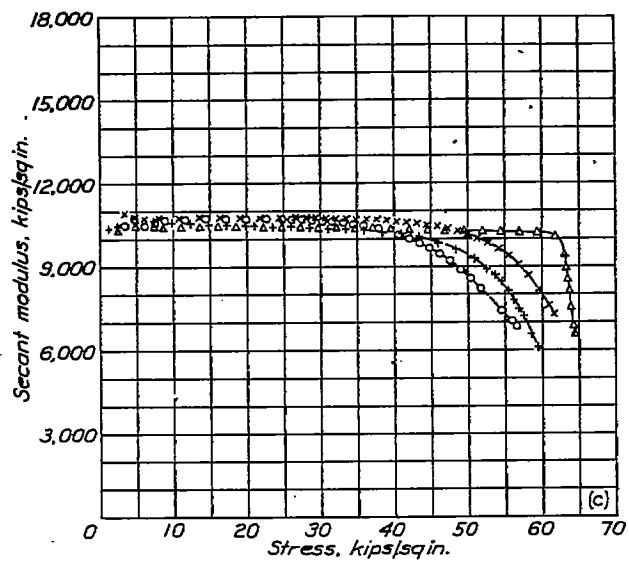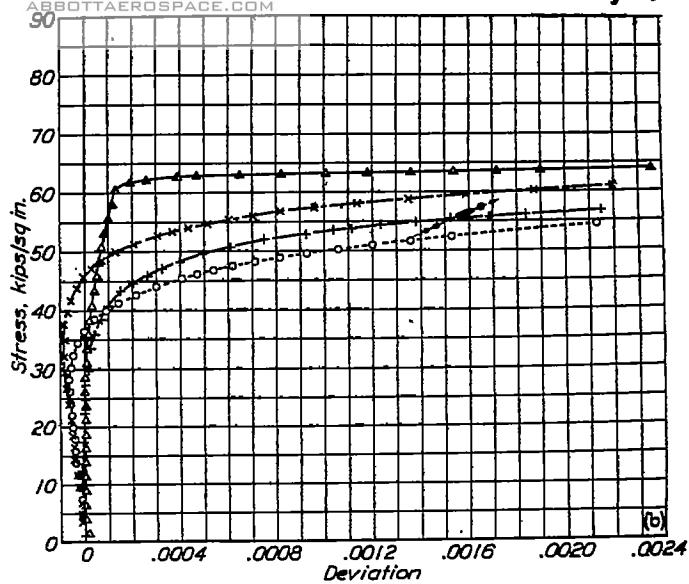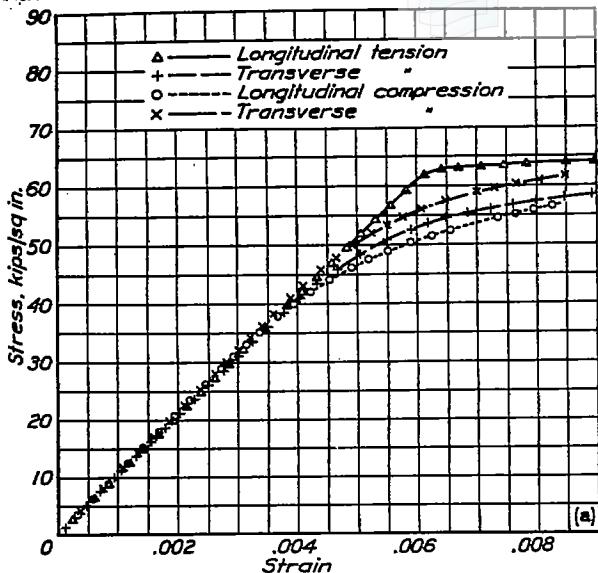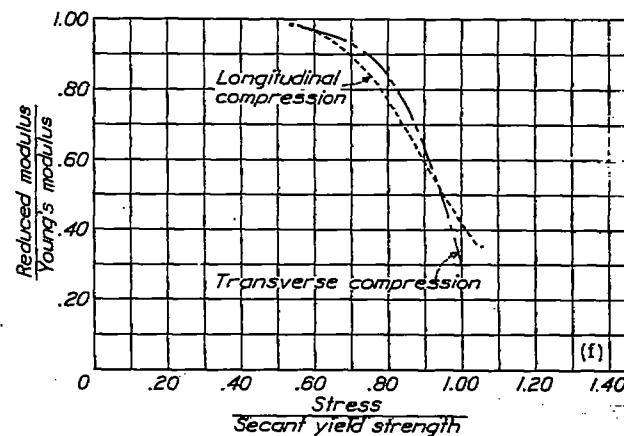
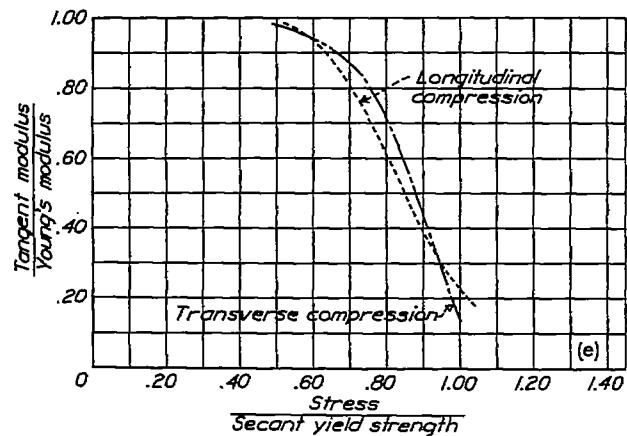
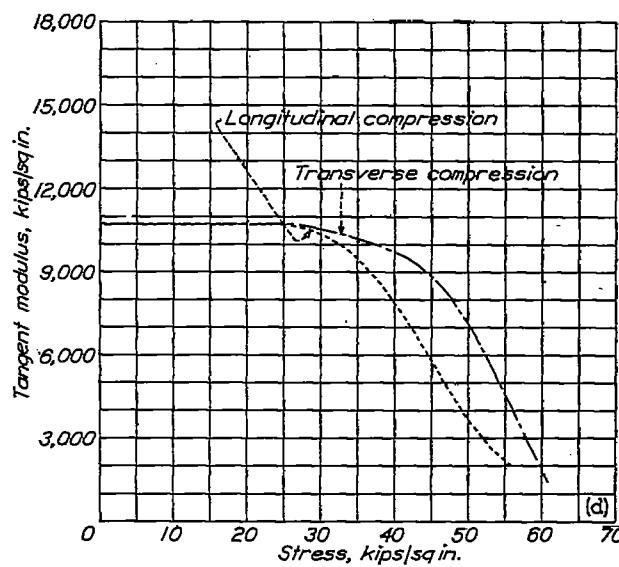
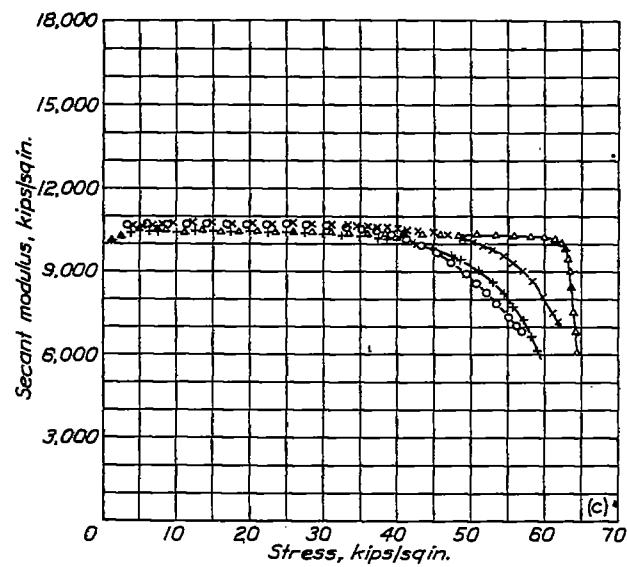
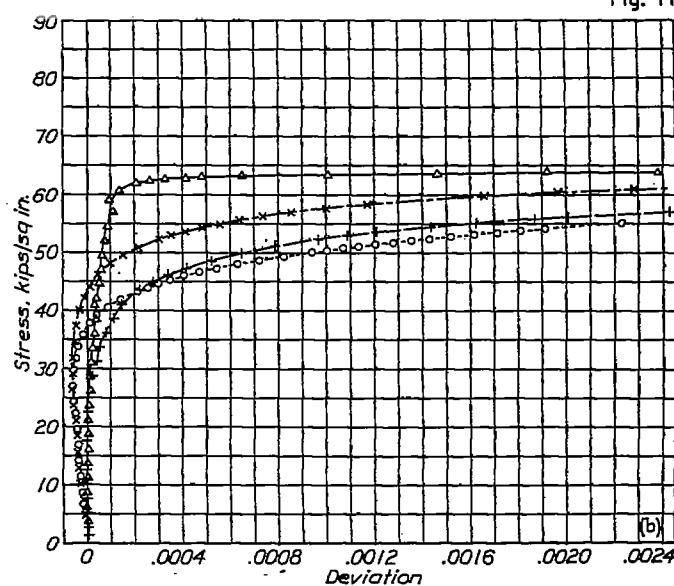
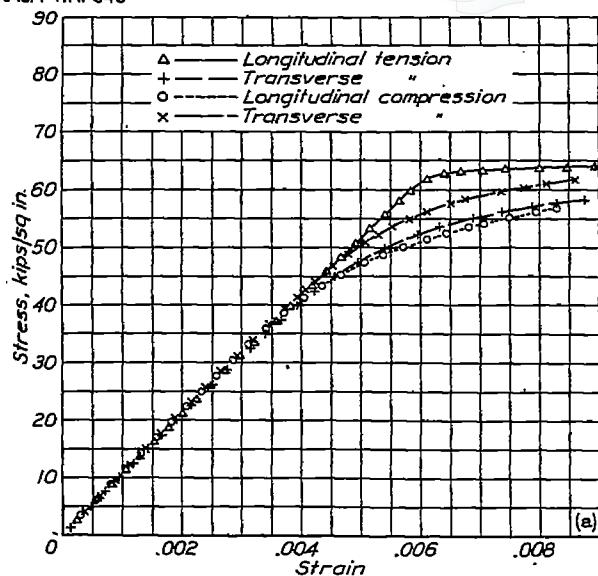


- (a) Stress-strain curves.
- (c) Secant modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
- (d) Tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.

Figure 11.- Sheet 11. Aluminum alloy 24S-RT; thickness, 0.081 inch.

NACA T.N. 840

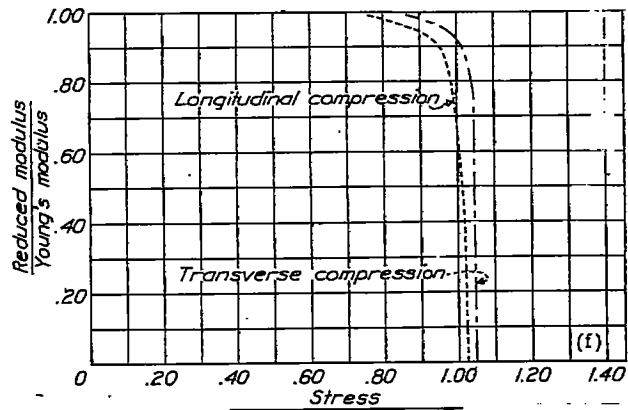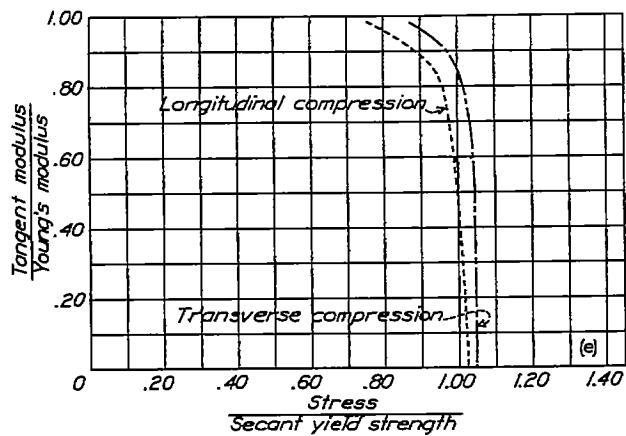
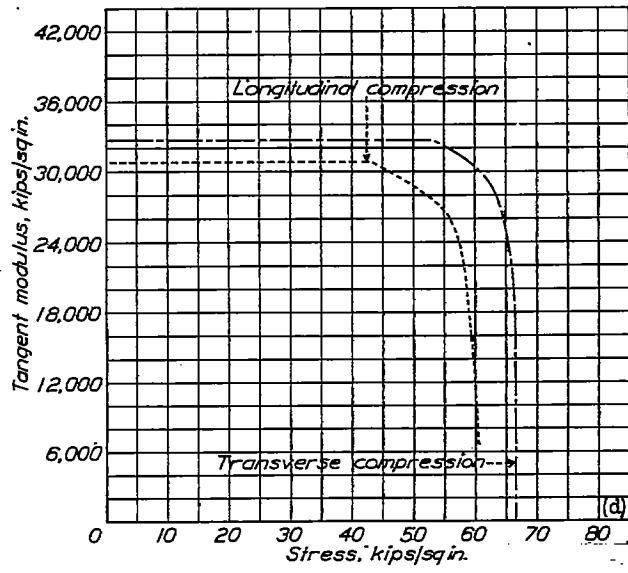
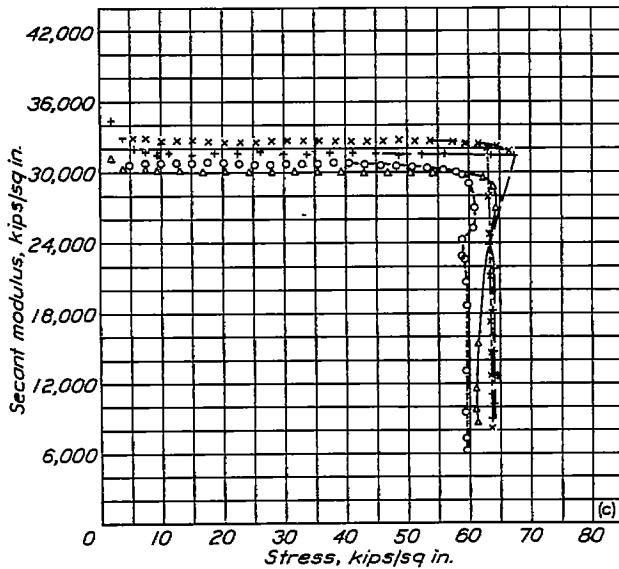
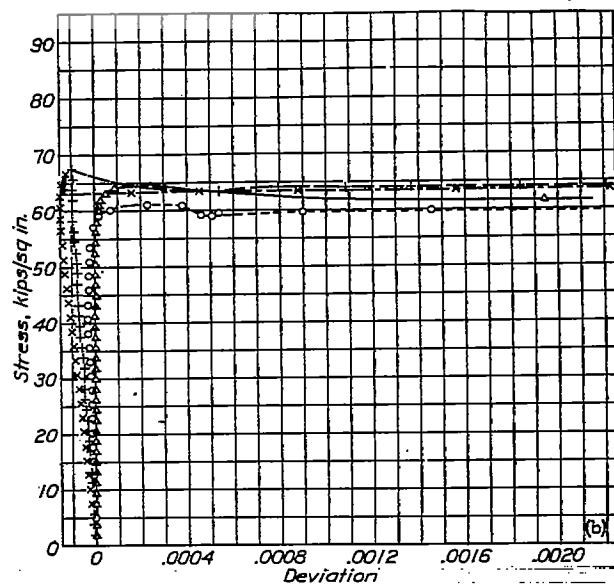
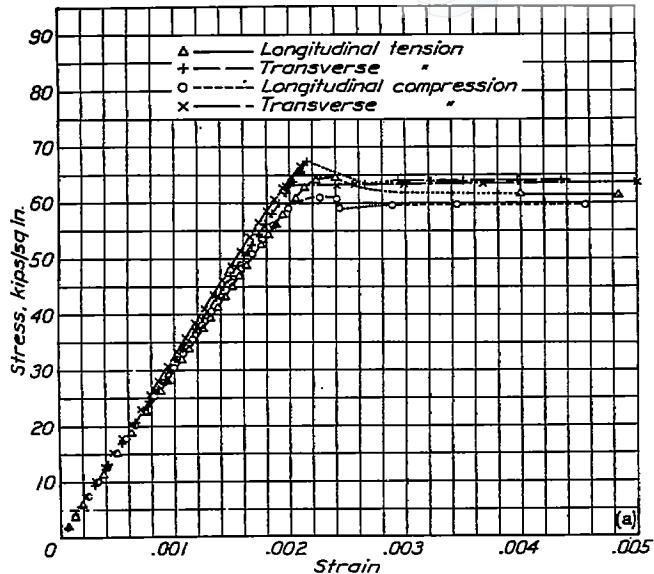


- (a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.


- (b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 12.- Sheet 12. 1025 carbon steel; thickness, 0.054 inch.

NACA T.N. 840

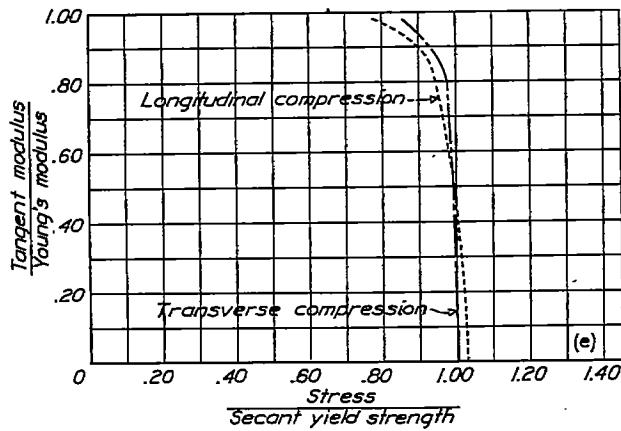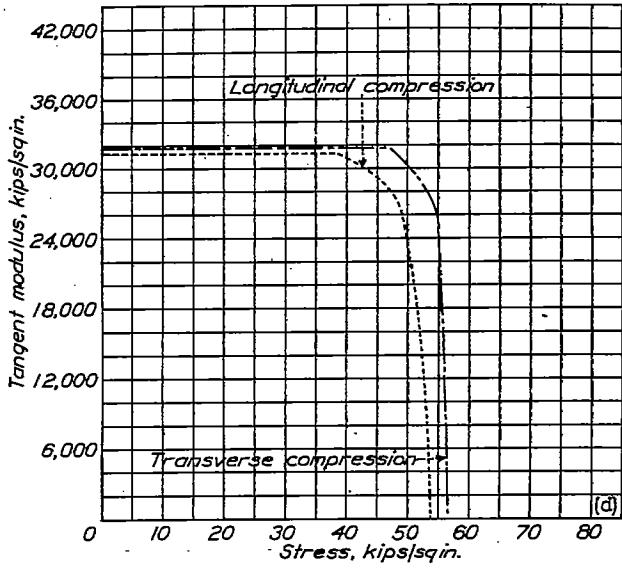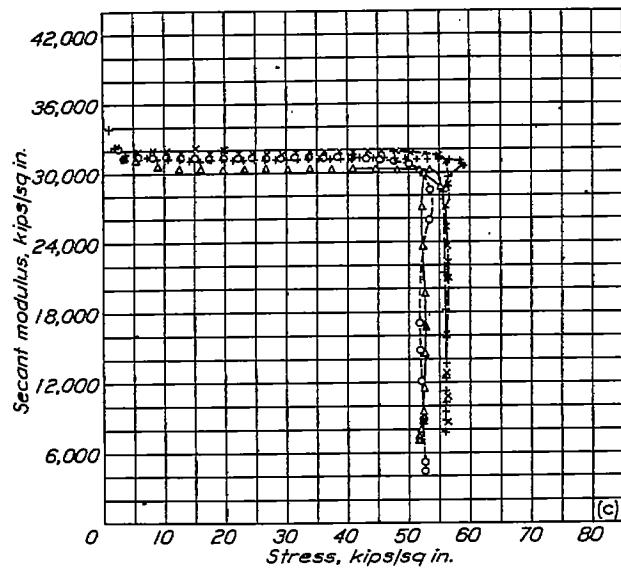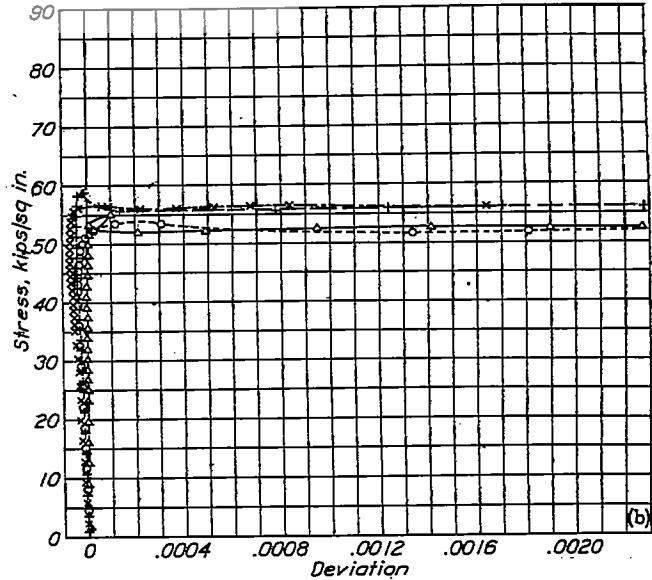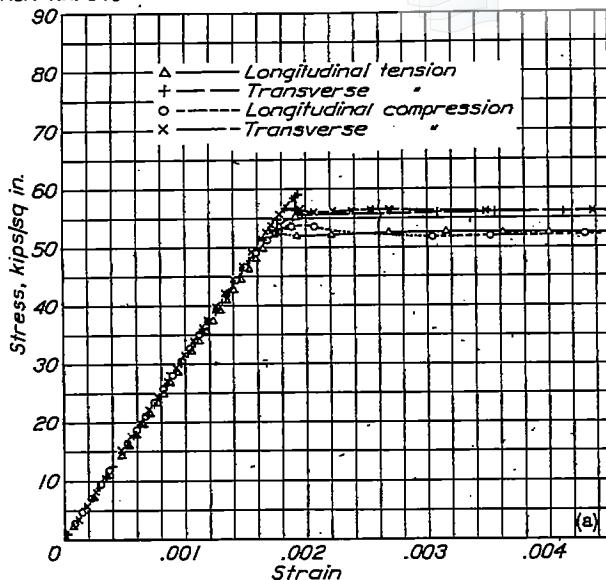







(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

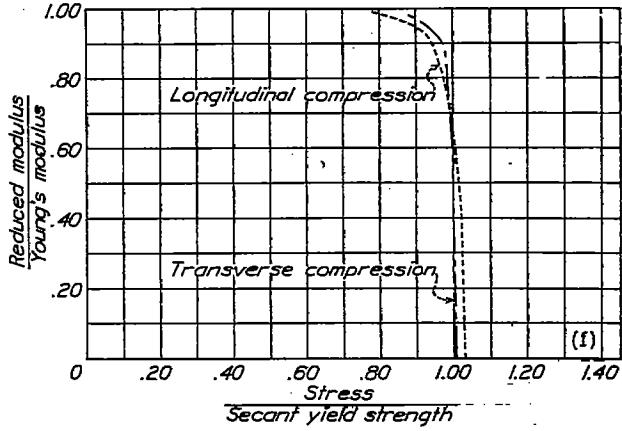

(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 13.- Sheet 13. 1025 carbon steel; thickness, 0.120 inch.







NACA T.N. 840

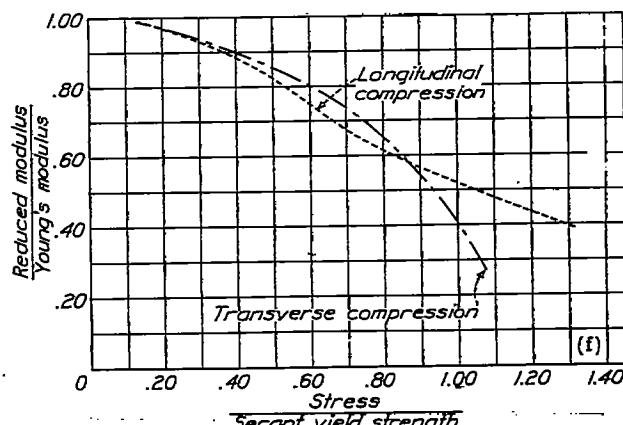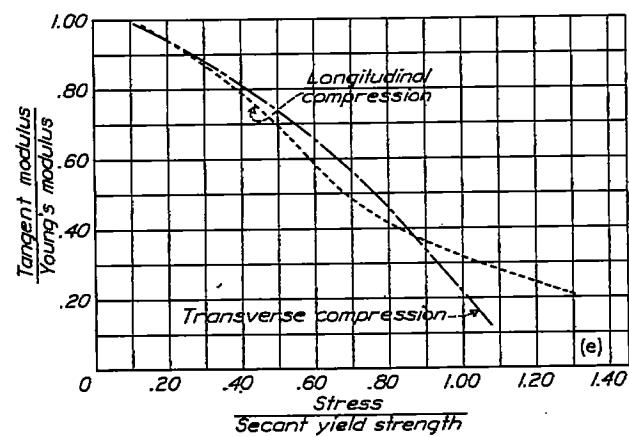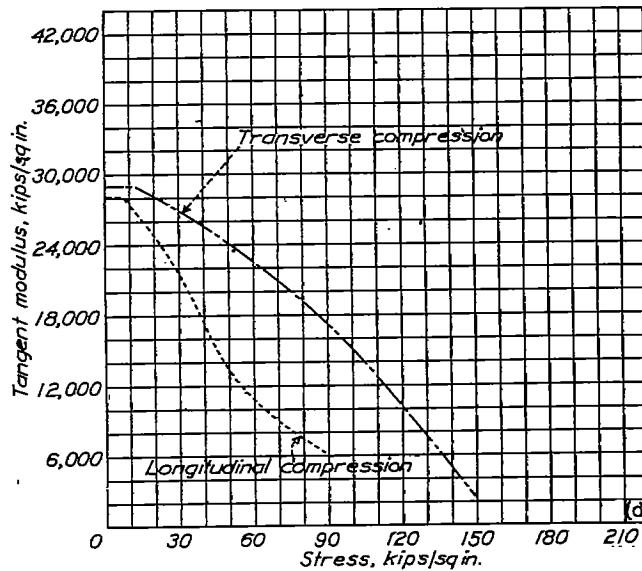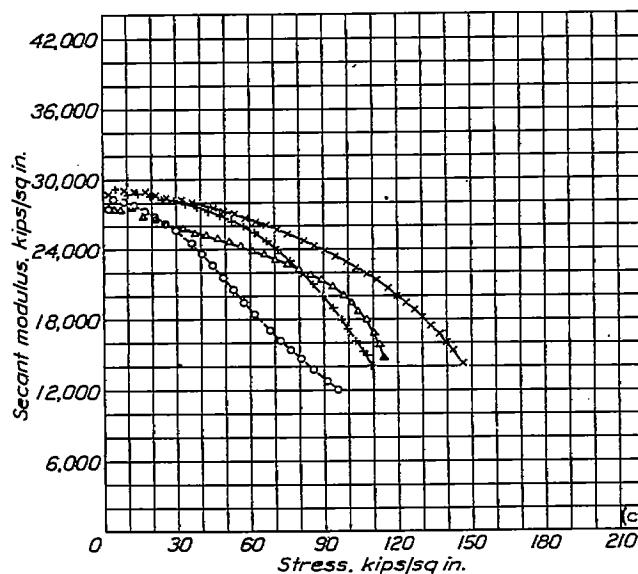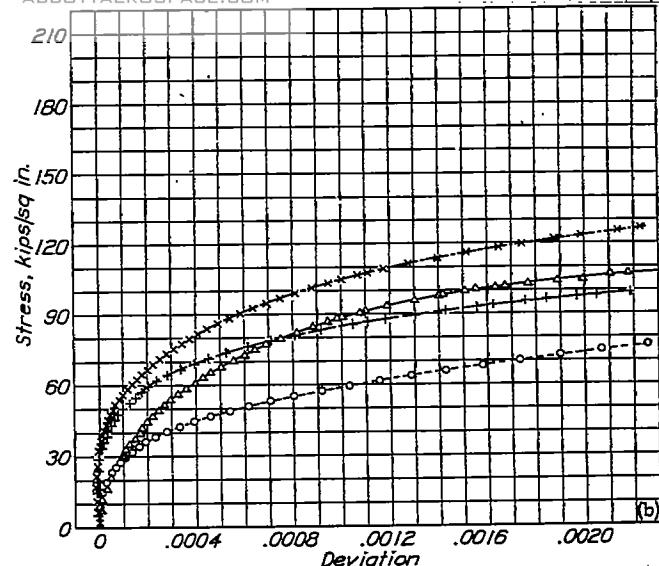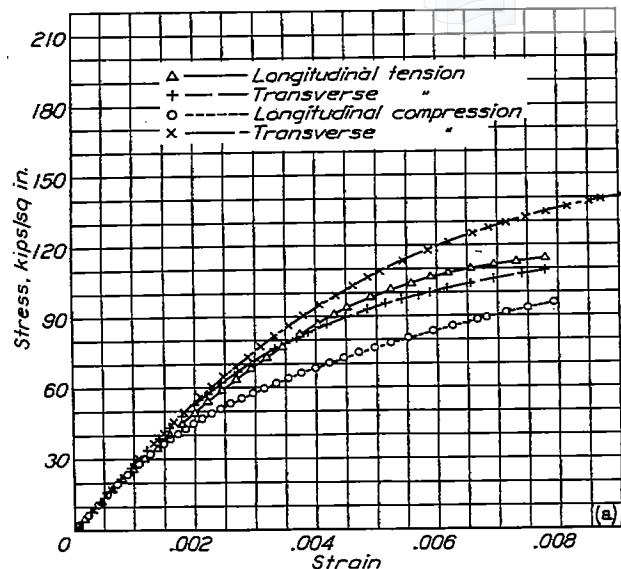

- (a) Stress-strain curves.
- (b) Stress-deviation curves.
- (c) Secant modulus-stress curves.
- (d) Tangent modulus-stress curves.
- (e) Nondimensional tangent modulus-stress curves.
- (f) Nondimensional reduced modulus-stress curves.







Figure 14.- Sheet 14, Chromium-nickel steel 1/4 hard; thickness, 0.020 inch.

NACA T.N. 840

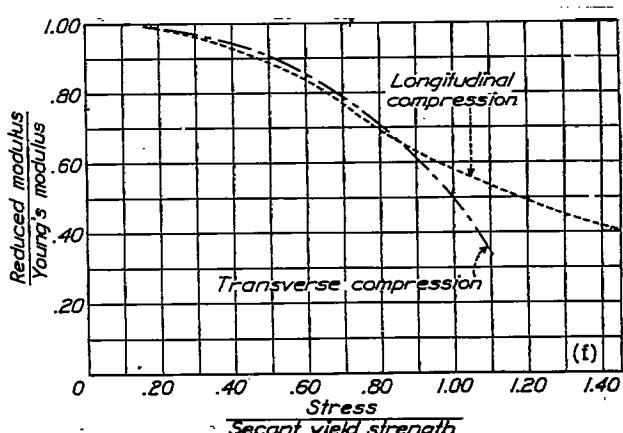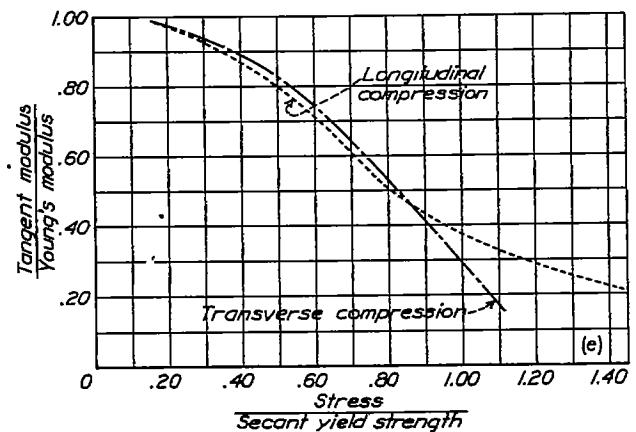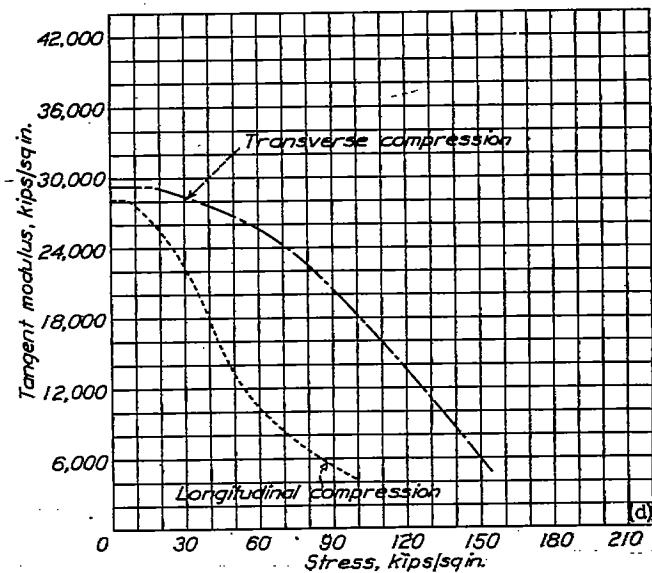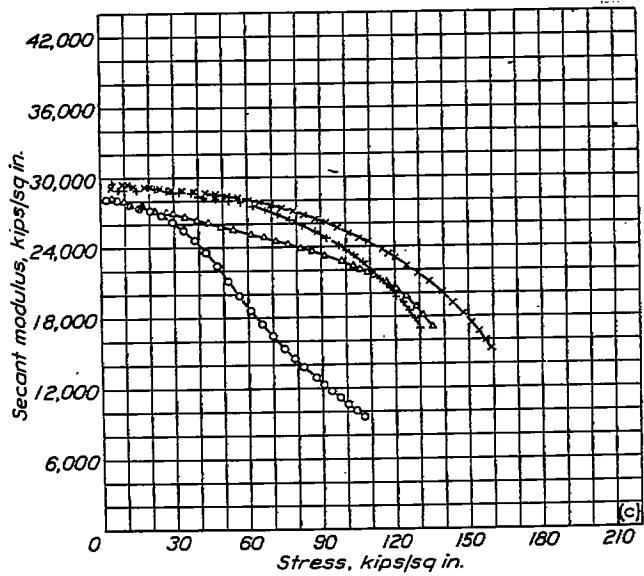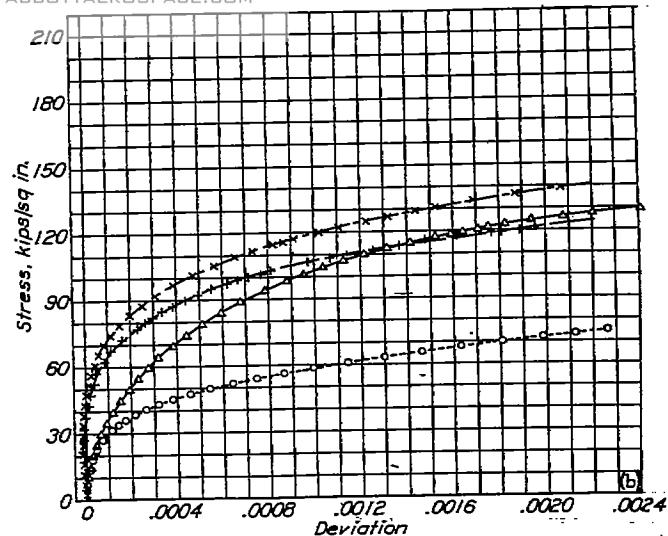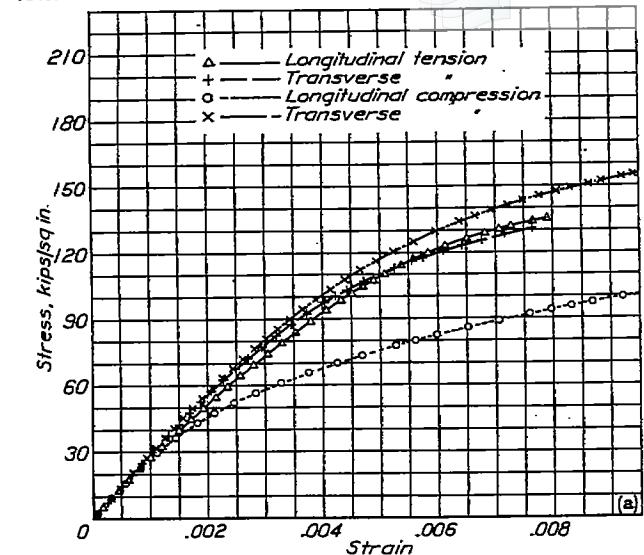

(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

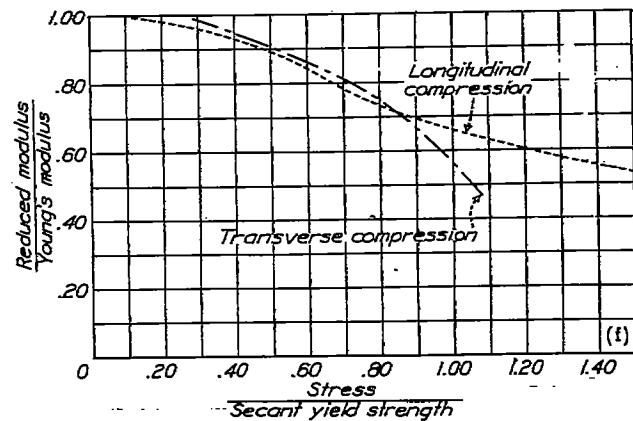
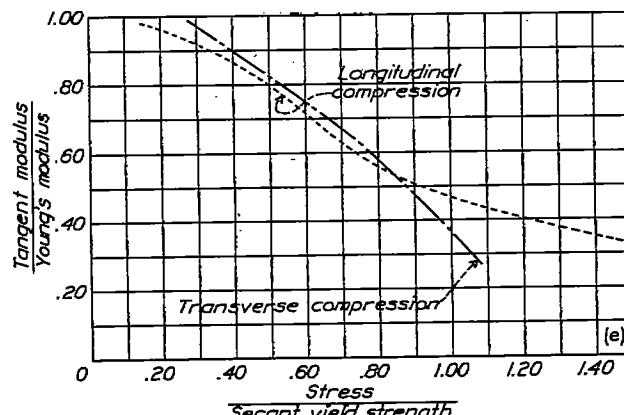
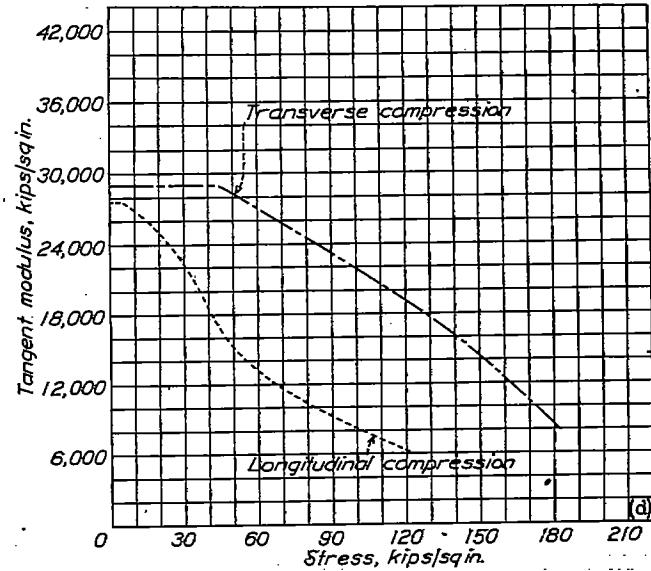
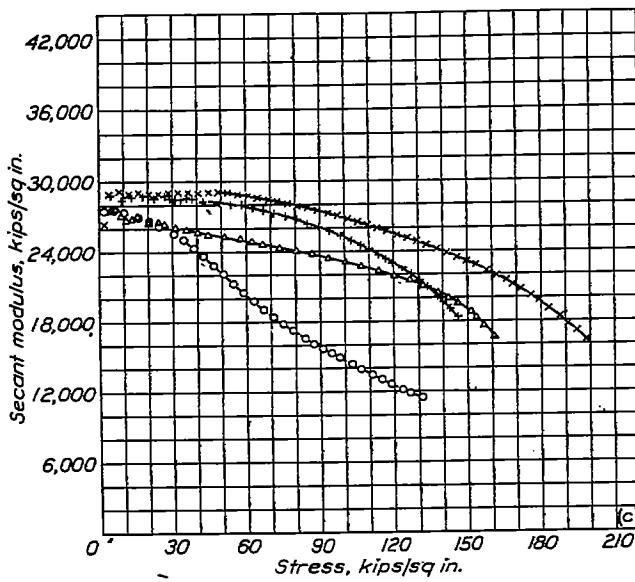
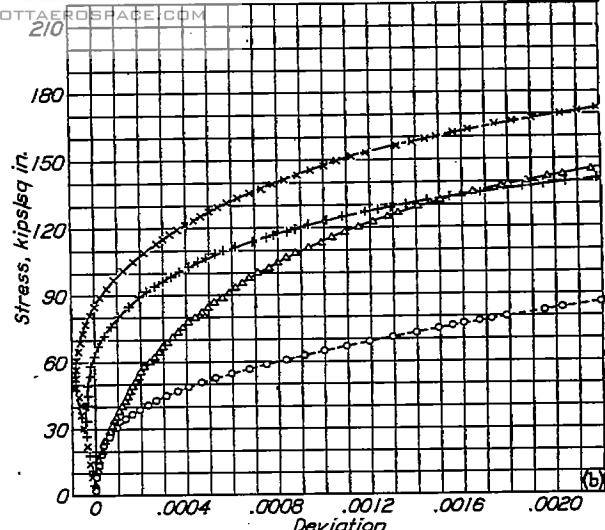
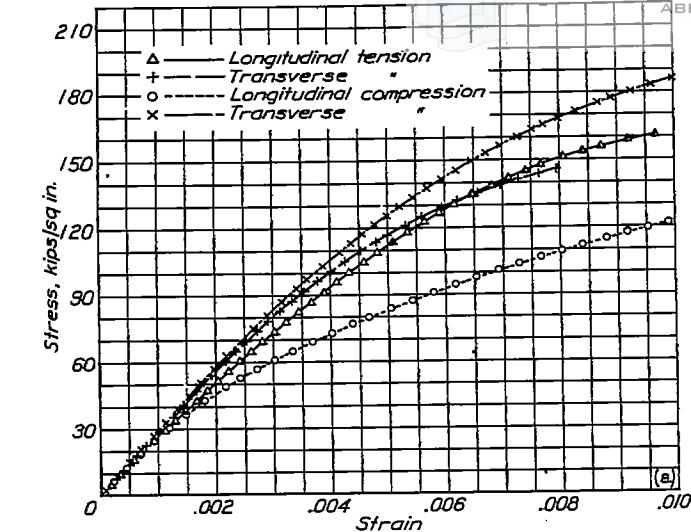


(a) Stress-strain curves.
(c) Secant modulus-stress curves.
(e) Nondimensional tangent modulus-stress curves.

(b) Stress-deviation curves.
(d) Tangent modulus-stress curves.
(f) Nondimensional reduced modulus-stress curves.

Figure 16.- Sheet 16. Chromium-nickel steel 3/4 hard; thickness, 0.020 inch.

NACA T.N. 840

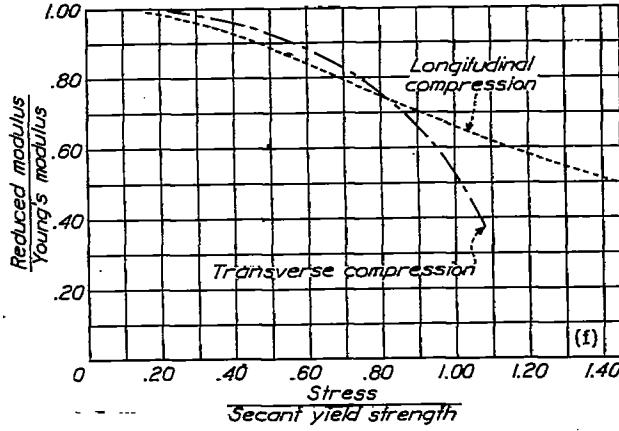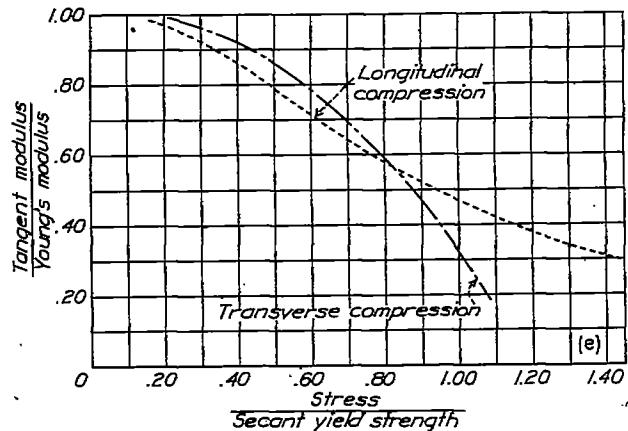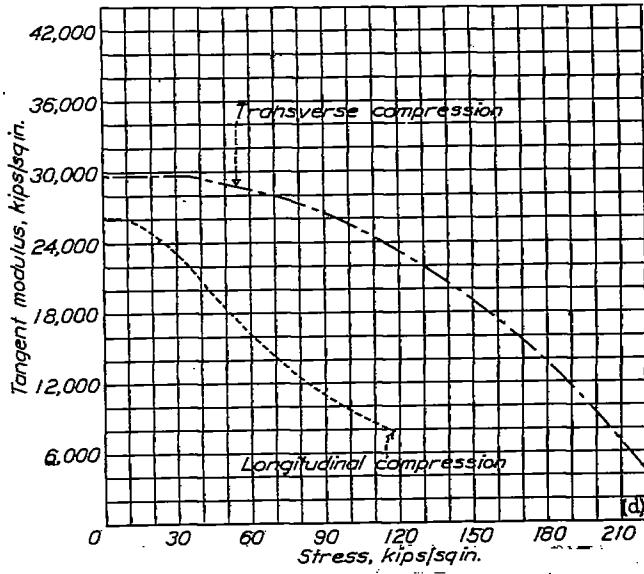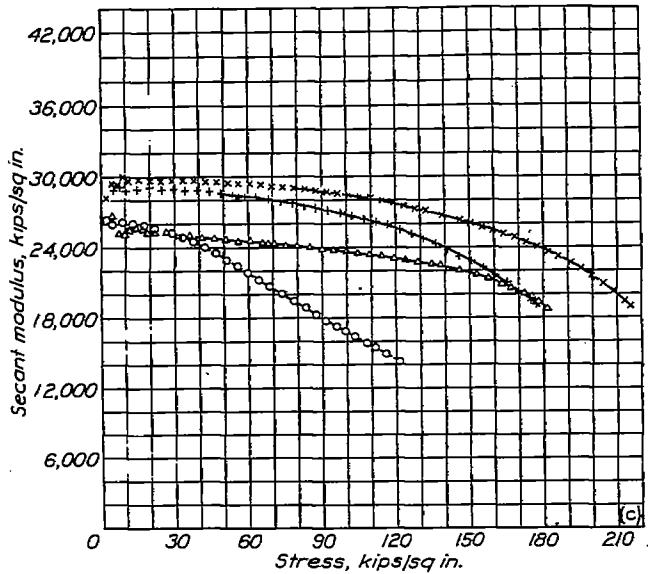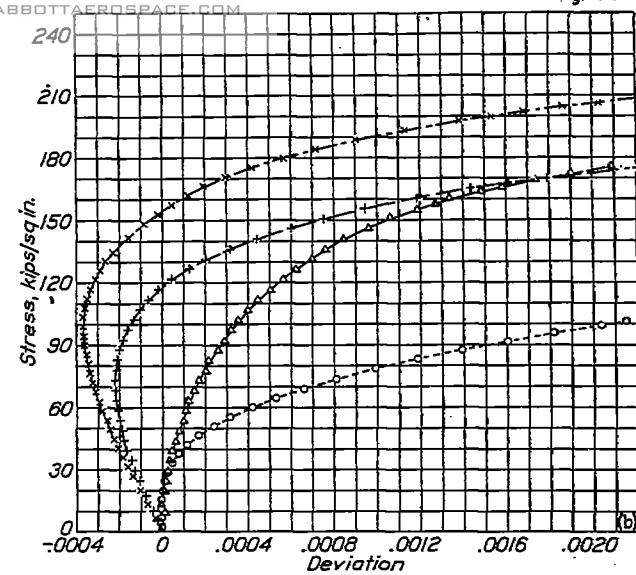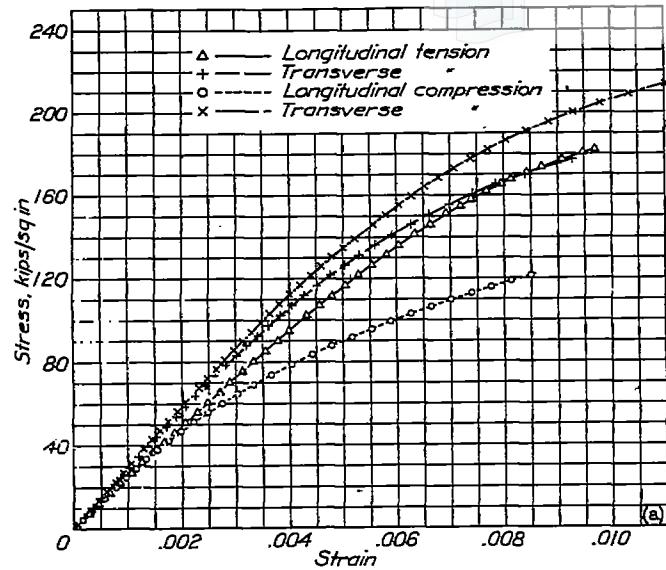







(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 17.- Sheet 17. Chromium-nickel steel full hard; thickness, 0.020 inch.

NACA T.N. 840

Fig. 18

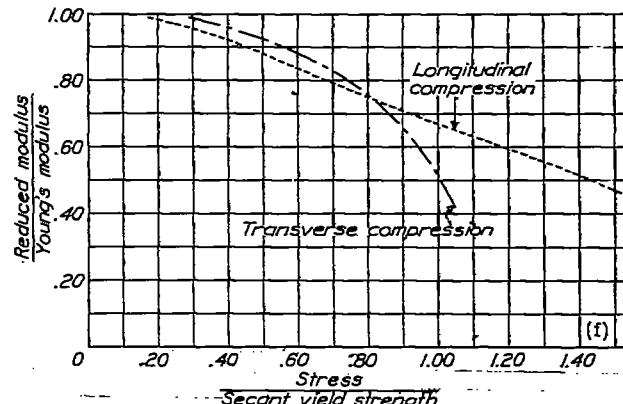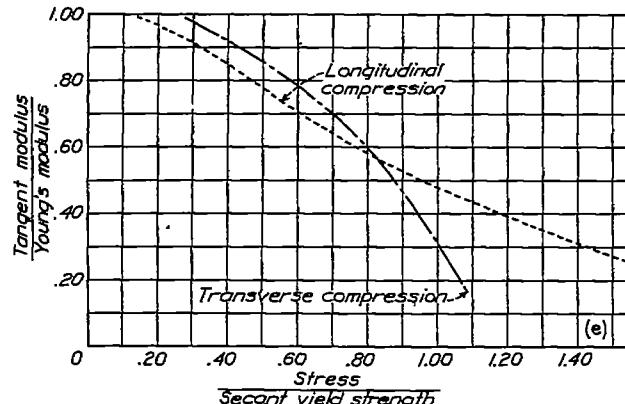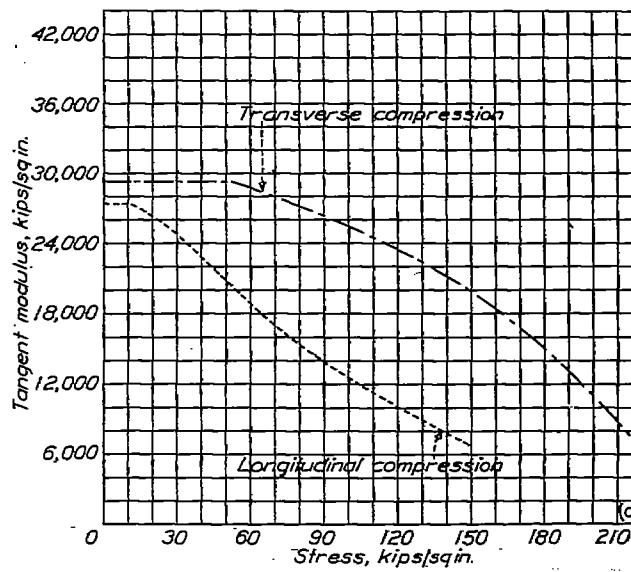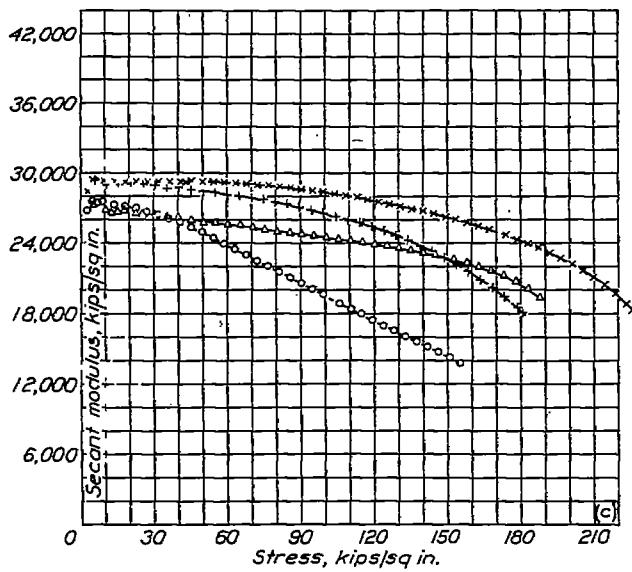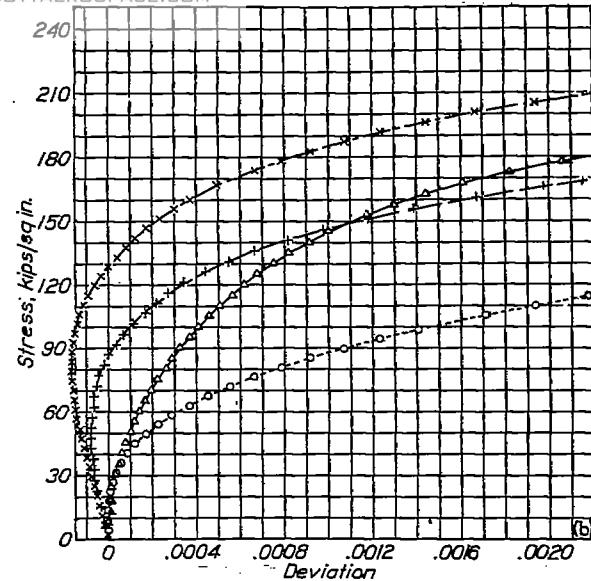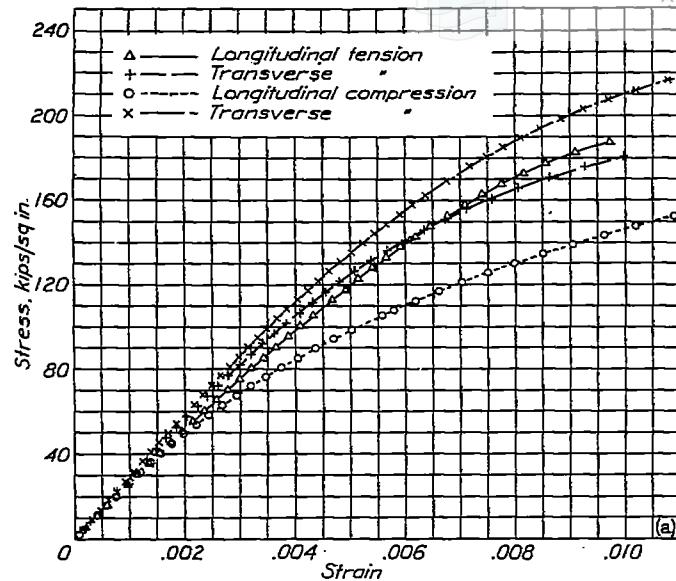

(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 18.- Sheet 18. Chromium-nickel steel full hard; thickness, 0.020 inch.

NACA T.N. 840












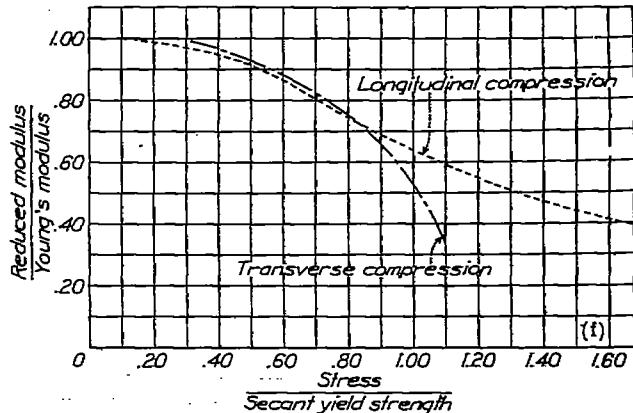


Figure 19.- Sheet 19. Chromium-nickel steel full hard; thickness, 0.024 inch.

(a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

(b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

NACA T.N. 840

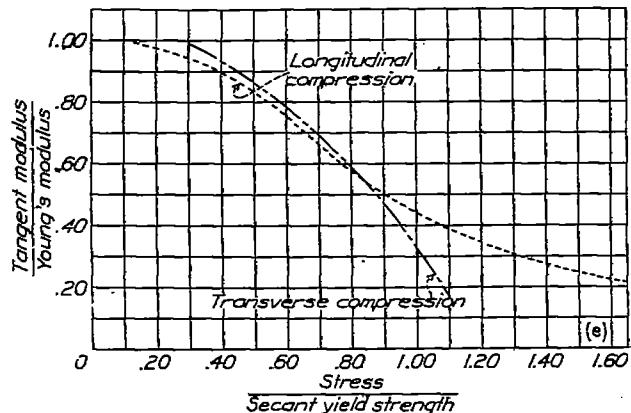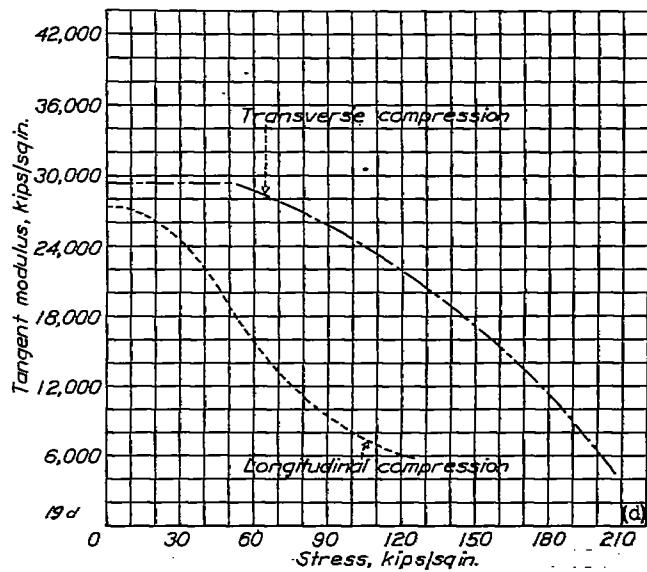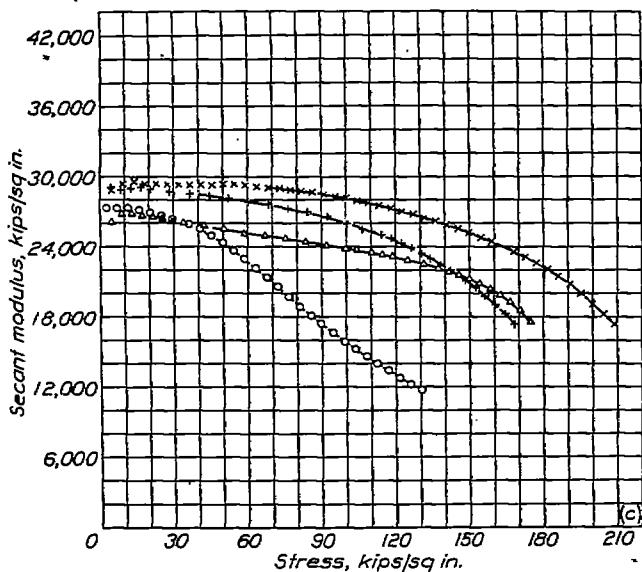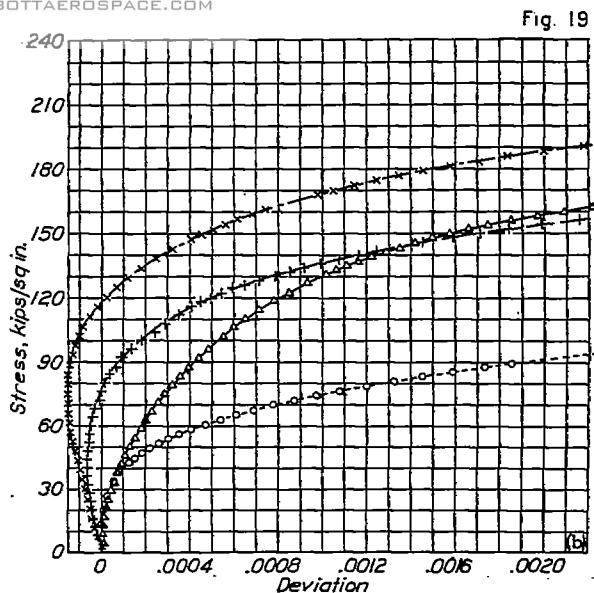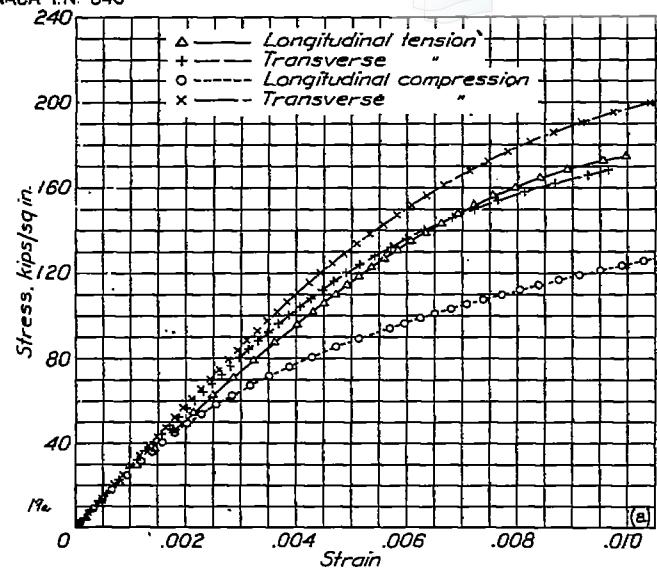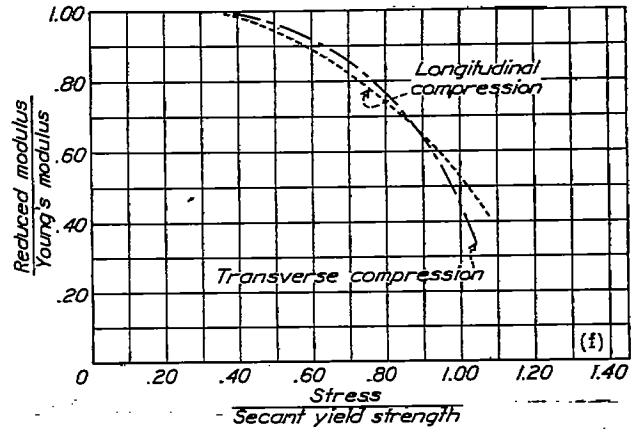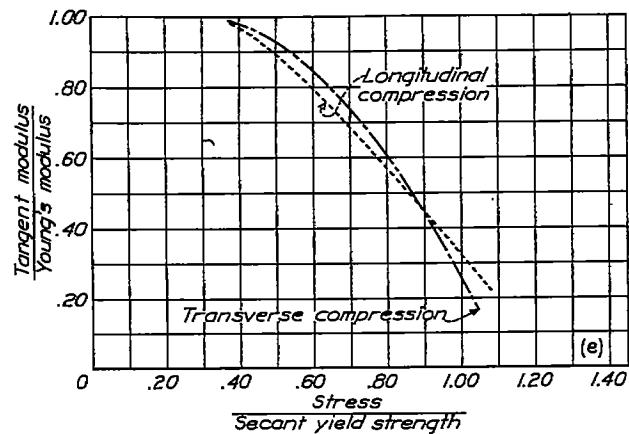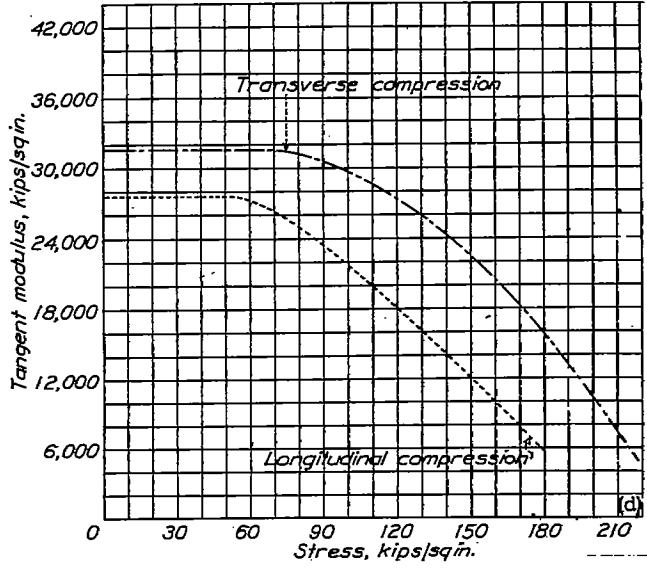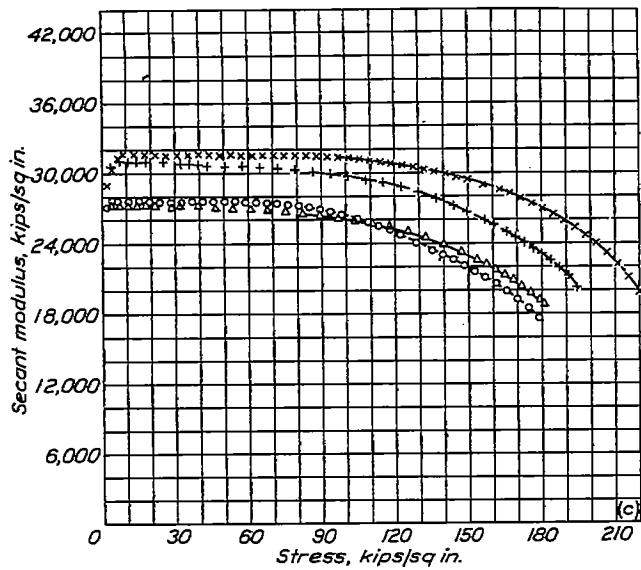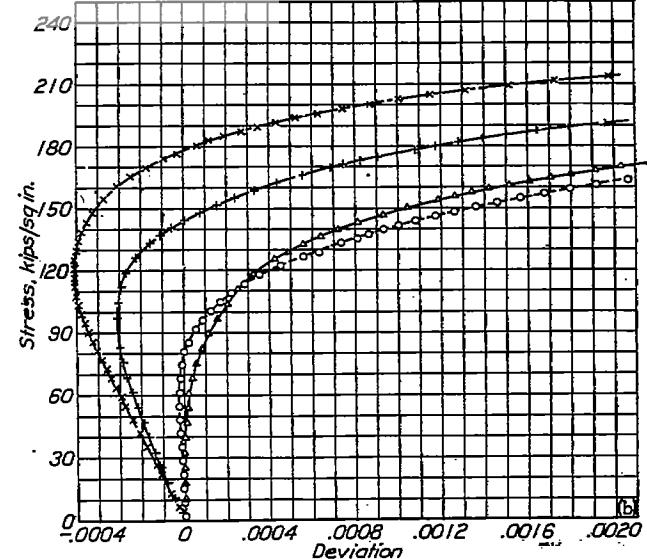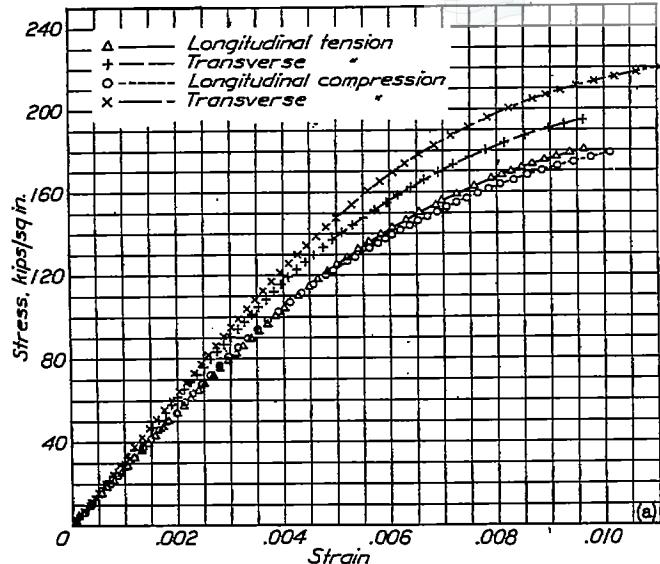

- (a) Stress-strain curves.
 (c) Secant modulus-stress curves.
 (e) Nondimensional tangent modulus-stress curves.

- (b) Stress-deviation curves.
 (d) Tangent modulus-stress curves.
 (f) Nondimensional reduced modulus-stress curves.

Figure 20.- Sheet 20. Chromium-nickel steel full hard; thickness, 0.0275 inch.